

## STRUCTURAL CHARACTERIZATION OF (Cu<sup>2+</sup>,Na<sup>+</sup>)- AND (Cu<sup>2+</sup>,NH<sub>4</sub><sup>+</sup>)-EXCHANGED BENTONITES UPON THERMAL TREATMENT

TORSTEN SEIFFARTH\* AND CHRISTIAN KAPS

Bauhaus University Weimar, Building Chemistry, Coudraystr. 13C, D-99423 Weimar, Germany

**Abstract**—Bentonites are excellent materials for sequestering various metal cations because of the cation fixation ability of the constituent montmorillonite layers, but sometimes, such as in the case of Cu<sup>2+</sup>, the exact location of cation fixation with respect to the clay layers is difficult to determine. Na-montmorillonite was prepared from the <2 μm fraction of the bentonite Calcigel (from Bavaria, Germany) and exchanged by Cu<sup>2+</sup> and Na<sup>+</sup> or by Cu<sup>2+</sup> and NH<sub>4</sub><sup>+</sup> cations. The resulting materials (bi-ionic Cu-Na and Cu-NH<sub>4</sub> samples, respectively, as well as homo-ionic forms with Cu<sup>2+</sup>, Na<sup>+</sup> and NH<sub>4</sub><sup>+</sup>) were heated for 24 h at temperatures of 300 and 450°C and the structural evolution characterized using X-ray diffraction (XRD) analysis, Fourier Transform Infrared (FTIR) spectroscopy, and differential scanning calorimetry (DSC) analysis.

The XRD patterns showed that the Cu sample and the Cu-Na sample have basal spacings of 12.5 Å. Upon heating at 300 and 450°C, the layers collapsed to 9.5 Å. In contrast, the *d*<sub>001</sub> value in the NH<sub>4</sub> sample and Cu-NH<sub>4</sub> sample decreased to 10.0 Å and 10.2 Å, respectively, during the heat treatment. The Cu<sup>2+</sup> ions migrated irreversibly into the montmorillonite structure.

For the NH<sub>4</sub> and the Cu-NH<sub>4</sub> samples, DSC analyses show that NH<sub>3</sub> evolved at between 300 and 400°C though the octahedral sheet was not altered substantially by the H<sup>+</sup> generated. Infrared spectra show that the bands of the Si-O and OH vibrations of all samples were changed upon heating due to the movement of the dehydrated cations into the hexagonal holes of the tetrahedral sheet. Apparently no Cu<sup>2+</sup> was trapped in the octahedral sheet. In the case of the Cu-NH<sub>4</sub> form, both Cu<sup>2+</sup> fixation and de-ammonization occurred during the heat treatment. Other than maintaining the basal spacing, no effect of the presence of NH<sub>4</sub><sup>+</sup> on the Cu<sup>2+</sup> fixation could be found for the montmorillonite studied.

**Key Words**—Acid Activation, Cu Fixation, De-ammonization, DRIFT, FTIR, Hofmann-Klemen Effect, Montmorillonite, NH<sub>4</sub> Clay.

### INTRODUCTION

The interaction of exchangeable heavy-metal cations (such as Cu<sup>2+</sup>) with the structures of clay minerals is of interest in the field of soil pollution, and in terms of using clays as barriers for waste disposal (Madejová *et al.*, 1999, 2006; Komadel, 2003).

Small cations (such as Li<sup>+</sup>, Cu<sup>2+</sup>) can be fixed in the clay mineral structure by thermal treatment. The movement of the interlayer cations into the structure leads to a loss of the swelling capacity and cation exchange capacity (CEC) of the clay mineral (Hofmann and Klemen, 1950; Greene-Kelly, 1952; Emmerich, 2000; Komadel *et al.*, 2005). If Cu<sup>2+</sup> is used as the fixing cation, however, the precise location of the fixed Cu<sup>2+</sup> in the clay mineral structure has yet to be established. Possible locations include the vacant octahedral sites (Mosser *et al.*, 1997; Shaiek *et al.*, 2003; Karmous *et al.*, 2006) or the bottom of the hexagonal cavities of the tetrahedral sheet (Tettenhorst, 1962; Karakassides *et al.*, 1999; Madejová *et al.*, 2006). It could also occupy both

sites (McBride and Mortland, 1974; Heller-Kallai and Mosser, 1995; He *et al.*, 2001).

The structural evolution of Cu<sup>2+</sup>-saturated homo-ionic forms of montmorillonite upon thermal treatment has been studied extensively by different methods, often by infrared (IR) spectroscopy (*e.g.* Madejová *et al.*, 1999). Only a few studies, however, have examined bi-ionic forms with various Cu<sup>2+</sup> contents (*e.g.* Oueslati *et al.*, 2006).

Another chemical modification of smectites is by acid activation, which is usually carried out by treatment with strong mineral acids. This treatment leads to dissolution of the octahedral sheet followed by a new arrangement of the structure to a framework of amorphous silica (Komadel, 2003). Acid-activated smectites are commonly used as catalysts and sorbents (such as bleaching earth) because of their large surface area and porosity (*e.g.* Chitnis and Sharma, 1997; Kaufhold and Decher, 2003).

The aim of the present study was to investigate the effect of the presence of NH<sub>4</sub><sup>+</sup> on the fixation of Cu<sup>2+</sup> during the thermal treatment of Cu-NH<sub>4</sub> montmorillonite at temperatures of 300 and 450°C: moderate internal acid activation with thermal assistance. If bentonite is saturated with Cu<sup>2+</sup> and NH<sub>4</sub><sup>+</sup>, then following thermal treatment, NH<sub>3</sub> is released in the temperature range from

\* E-mail address of corresponding author:  
torsten.seiffarth@bauing.uni-weimar.de  
DOI: 10.1346/CCMN.2009.0570104

300 to 400°C and protons are generated in the interlayer and on the outer surface, as shown in equation 1 (according to Wright *et al.*, 1972).



This moderate acid activation can result in partial alteration of the clay mineral structure. Previously exchangeable Cu<sup>2+</sup> can be fixed in the structure under these conditions.

Preliminary investigations were carried out by extraction experiments of heated Cu-Ca and Cu-NH<sub>4</sub> bentonites by treating 0.5 g of solid material with 25 mL of 1 M CH<sub>3</sub>COONH<sub>4</sub> solution for 2 h (three times). The total amount of Cu<sup>2+</sup> in both samples was 36 meq/100 g before the extraction experiments. The Cu<sup>2+</sup> extraction rates of the Cu-Ca and Cu-NH<sub>4</sub> bentonites after thermal treatment at 400°C were determined to be 27% and 3%, respectively, meaning that the extraction rate of Cu<sup>2+</sup> is markedly decreased by the presence of NH<sub>4</sub><sup>+</sup> during the thermal treatment, in contrast to an ordinary thermal treatment in the absence of NH<sub>4</sub><sup>+</sup> (Seiffarth and Kaps, 2005).

## MATERIALS AND METHODS

The starting material, a Na homo-ionic form of montmorillonite was prepared from the <2 μm fraction of the bentonite 'Calcigel' from the clay deposit in Bavaria (Germany). The chemical compositions of the untreated and purified materials were determined using a C and S analyser and inductively-coupled plasma optical emission spectroscopy (ICP-OES) with an ICP Optima 3000 instrument (Table 1). The chemical pre-treatment

Table 1. Chemical composition (wt.%) of the bentonite Calcigel before and after pre-treatment.

	Raw sample (before pre-treatment)	<2 μm fraction (after pre-treatment)
LOI	17.1	13.4
SiO <sub>2</sub>	50.2	55.3
Al <sub>2</sub> O <sub>3</sub>	17.2	19.0
Fe <sub>2</sub> O <sub>3</sub>	4.6	5.8
CaO	4.1	0.0
MgO	4.3	3.2
TiO <sub>2</sub>	0.26	0.24
MnO	0.04	0.02
K <sub>2</sub> O	1.4	0.98
Na <sub>2</sub> O	0.33	1.95
P <sub>2</sub> O <sub>5</sub>	0.1	0.06
SO <sub>3</sub> (sulfate)	0.1	no data
S (sulfide)	0.05	no data
TOC	0.18	no data
TIC	0.82	no data

LOI = loss on ignition  
TOC = total organic carbon  
TIC = total inorganic carbon

of the bentonite to eliminate carbonate, Fe oxide, Al hydroxide, and organic matter was carried out according to Mehra and Jackson (1960), Tributh and Lagaly (1986), and Wolters (2005). The <2 μm fraction was obtained from the purified samples by sedimentation. X-ray diffraction patterns showed that smectite is the dominant mineral in this fine fraction, though impurities of quartz, feldspar, mica, and minor carbonate were identified. The <2 μm samples were saturated with Na<sup>+</sup> by treatment with NaCl and washed free of excess salts, dried at 60°C, powdered gently in a mortar, and divided into several portions. One portion was mixed with a 0.01 M CuCl<sub>2</sub> solution (1 g, 25 mL, 2 h, once) in order to obtain a montmorillonite exchanged with Cu<sup>2+</sup> and Na<sup>+</sup>. Another portion was initially transformed to a Cu homo-ionic form, by treatment with a 0.02 M CuCl<sub>2</sub> solution (1 g, 25 mL, 2 h, five times), some of which was mixed subsequently with 0.5 M CH<sub>3</sub>COONH<sub>4</sub> solution (1 g, 25 mL, 2 h, once) to produce a montmorillonite exchanged with Cu<sup>2+</sup> and NH<sub>4</sub><sup>+</sup>. In addition, a homo-ionic NH<sub>4</sub><sup>+</sup> form was prepared by treatment with a 1 M CH<sub>3</sub>COONH<sub>4</sub> solution (1 g, 25 mL, 2 h, five times). After each step the samples were washed free of excess salts, dried, and powdered as mentioned previously. All solutions were analyzed for Cu<sup>2+</sup> and Na<sup>+</sup> content, before and after an application, by ICP-OES. The Cu<sup>2+</sup> content of the resulting Cu-Na and Cu-NH<sub>4</sub> samples was determined to be 30 meq/100 g and 20 meq/100 g, respectively. The total CEC is 60 meq/100 g, measured by the complete treatment with CH<sub>3</sub>COONH<sub>4</sub> solutions as well as with CuCl<sub>2</sub> solutions.

Five differently exchanged samples, homo-ionic forms with Na<sup>+</sup>, Cu<sup>2+</sup>, NH<sub>4</sub><sup>+</sup>, and bi-ionic forms with (Cu<sup>2+</sup>,Na<sup>+</sup>) and (Cu<sup>2+</sup>,NH<sub>4</sub><sup>+</sup>), were available for investigation. The materials were heated for 24 h at temperatures of 300 and 450°C (laboratory furnace, corundum vessels, air atmosphere).

The powder XRD patterns were recorded over the range 4–70°2θ using a Seifert 3003 TT diffractometer (CuKα radiation).

Fourier transform infrared attenuated total reflectance (FTIR-ATR) spectra in the 4000–400 cm<sup>-1</sup> spectral range were obtained on a FTS 175C Biorad infrared spectrometer, using the DuraSampl technique. In addition, diffuse reflectance infrared spectroscopy (DRIFT) was used for detailed measurements in the Si–O stretching region (1300–400 cm<sup>-1</sup>). Samples of 4 mg were ground slightly with 400 mg of KBr, and the resulting powders poured loosely into the sample cup.

The thermal behavior of the solid samples was studied by DSC using a Setsys 16/18 device (Setaram).

## RESULTS AND DISCUSSION

### Thermal analyses

The DSC curves of the Cu-Na montmorillonite and Cu-NH<sub>4</sub> montmorillonite (Figure 1) revealed that heat-

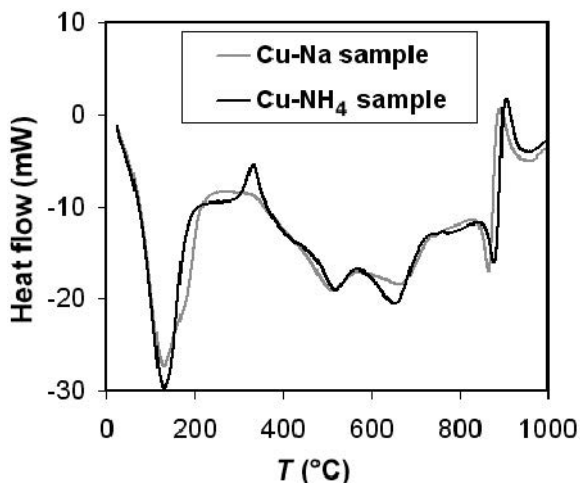


Figure 1. DSC curves of the Cu-Na- and Cu-NH<sub>4</sub>-montmorillonites (40 mg, 10 K/min, Pt crucible, air atmosphere).

ing of the Cu-NH<sub>4</sub> sample leads to an exothermic peak between 300 and 400°C due to the de-ammonization of the NH<sub>4</sub><sup>+</sup>, unlike the Cu-Na sample. The exothermic effect probably results from an intracrystalline oxidation of the NH<sub>4</sub><sup>+</sup> upon thermal treatment in an oxidizing atmosphere, according to Barrer (1949), who described this effect for NH<sub>4</sub><sup>+</sup> zeolites. No exothermic effect could be found by DSC in an argon atmosphere.

Dehydroxylation of the montmorillonite investigated occurred in two steps (520–670°C). Dioctahedral 2:1 clay minerals containing *trans*-vacant and *cis*-vacant varieties in their octahedral sheet (mixed type) have two dehydroxylation peaks (Wolters and Emmerich, 2007). The presence of NH<sub>4</sub><sup>+</sup> in the montmorillonites led to a decrease in the dehydroxylation temperature (*cis*). This is probably caused by the effect of the H<sup>+</sup> generated in the octahedral sheet after the de-ammonization of the NH<sub>4</sub><sup>+</sup>.

#### XRD data

The  $d_{001}$  values of the bi-ionic Cu-Na montmorillonite and the Cu-NH<sub>4</sub> montmorillonite at different temperatures (Table 2) indicate that unheated samples have basal spacings of 12.5 Å (Cu-Na) and 12.2 Å (Cu-NH<sub>4</sub>). The smaller basal spacing for the Cu-NH<sub>4</sub> form is probably caused by the nature of the NH<sub>4</sub><sup>+</sup> cation that fits into the hexagonal cavities. Upon heating at 300

Table 2.  $d_{001}$  values (in Å) of the dry-powder samples of bi-ionic Cu-Na and Cu-NH<sub>4</sub> in addition to homo-ionic Cu- and NH<sub>4</sub>-montmorillonite at different temperatures.

Starting sample	60°C	300°C	450°C
Cu-Na	12.5	9.5	9.5
Cu-NH <sub>4</sub>	12.2	10.2	10.0
Cu	12.5	9.5	9.5
NH <sub>4</sub>	12.2	10.0	10.0

and 450°C the layers of the Cu-Na sample collapsed to 9.5 Å, in accordance with previous studies (Mosser *et al.*, 1997; Emmerich, 2000; Shaiek *et al.*, 2003; Karmous *et al.*, 2006) and is caused by the irreversible migration of the Cu<sup>2+</sup> cations into the montmorillonite structure during the thermal treatment (the ‘Hofmann-Klemen effect’). In contrast, the  $d_{001}$  value of the Cu-NH<sub>4</sub> sample only decreased to 10.0 Å upon heating. The amount of Cu<sup>2+</sup> in the Cu-Na form was greater than that of the Cu-NH<sub>4</sub> form. This could be a reason for the different  $d_{001}$  values of the samples heated at 300°C when NH<sub>4</sub><sup>+</sup> was still present in the interlayer. For samples heated at 450°C, little or no NH<sub>4</sub><sup>+</sup> existed in the interlayer, as confirmed by DSC and FTIR. However, moderate acid activation can lead to partial dissolution of the octahedral sheet so that cations from the structure are present in the interlayer. For instance, the amount of exchangeable Al<sup>3+</sup> was 12 meq/100 g when 0.1 g of heated NH<sub>4</sub> sample (450°C) was treated with 25 mL of 0.02 M CuCl<sub>2</sub> solution (pH 4.2) for 2 h (three times).

The XRD patterns (Table 2) of the homo-ionic Cu and NH<sub>4</sub> forms at different temperatures show, however, features like those of the comparable bi-ionic forms. The basal spacing of the thermally treated NH<sub>4</sub> form (10.0 Å) is greater than for the Cu form (9.5 Å) for treatments at 300°C as well as at 450°C. Obviously, the de-ammonization of the NH<sub>4</sub> sample had already begun by 300°C. However, for clay minerals such as vermiculite with a different octahedral-sheet composition and greater layer charge than for the montmorillonite in the present case, NH<sub>4</sub><sup>+</sup> cations remained in the interlayer after treatments above 450°C (Poyato *et al.*, 2002; Pérez-Maqueda *et al.*, 2003; Pérez-Rodríguez *et al.*, 2004).

#### FTIR data

Absorption bands representing vibrational modes in the Si-O stretching, Si-O bending, and O-H bending regions (1300–400 cm<sup>-1</sup>) were obtained by the DRIFT technique for the bi-ionic Cu-Na and Cu-NH<sub>4</sub> montmorillonites at different temperatures (Figures 2) and for the homo-ionic Na-, Cu-, and NH<sub>4</sub>-montmorillonites (Figure 3). The OH- and NH-stretching regions (4000–1400 cm<sup>-1</sup>) were probed using the FTIR-ATR method (Figure 4).

*Si-O vibrations.* The broad band at 1050 cm<sup>-1</sup>, including a shoulder at 1115 cm<sup>-1</sup>, is assigned to the Si–O stretching vibration in the tetrahedral sheet of the unheated samples (Farmer, 1974). The migration of Cu<sup>2+</sup> from the interlayer into the hexagonal cavities of the tetrahedral sheet or into vacant octahedral sites affected the Si–O vibrations, in that the Si–O bands in Cu-samples shifted to greater frequencies upon heating, which is consistent with previous studies (Madejová *et al.*, 1999, 2006). Cu-Na and Cu-NH<sub>4</sub> samples showed a shift in the Si–O stretching band to 1058 cm<sup>-1</sup> and the appearance of a shoulder at 1120 cm<sup>-1</sup> after heating at

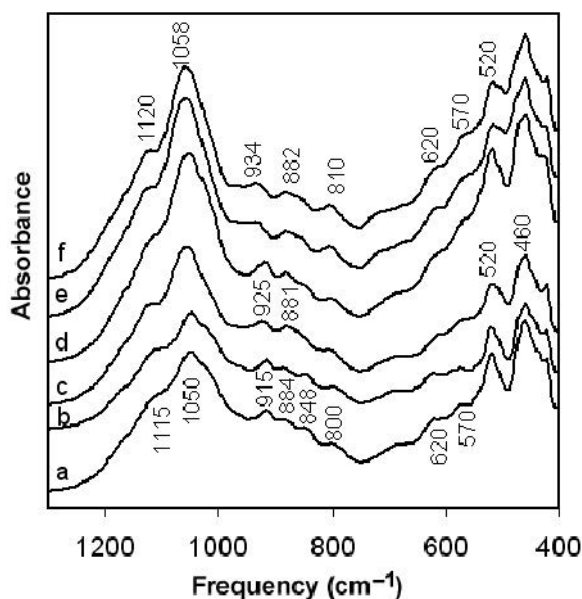


Figure 2. DRIFT spectra of bi-ionic Cu-Na- and Cu-NH<sub>4</sub>-montmorillonites at different temperatures: Cu-Na 60°C (a), Cu-NH<sub>4</sub> 60°C (b), Cu-Na 300°C (c), Cu-NH<sub>4</sub> 300°C (d), Cu-Na 450°C (e), and Cu-NH<sub>4</sub> 450°C (f).

300 and 450°C.

The positions of the Si–O bending vibrations at 620, 520, and 460 cm<sup>-1</sup> were mainly unchanged. In all samples some decrease in the intensity of the Si–O–Al bands near 620 and 520 cm<sup>-1</sup> was identified upon

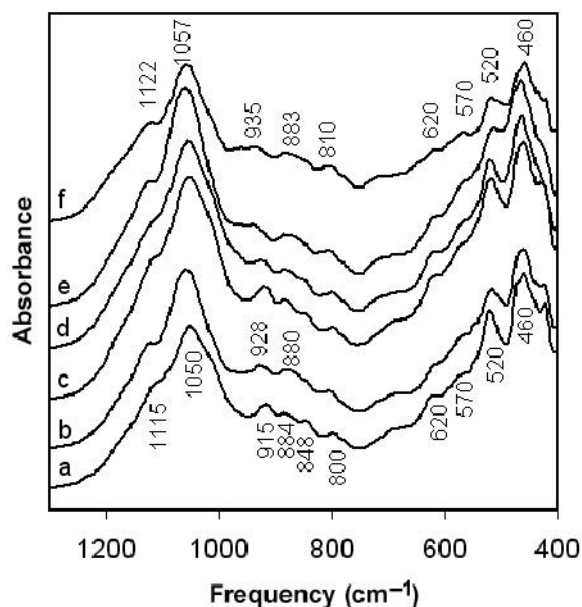


Figure 3. DRIFT spectra of homo-ionic Na-, Cu-, and NH<sub>4</sub>-montmorillonites at different temperatures: Na 300°C (a), Cu 300°C (b), NH<sub>4</sub> 300°C (c), Na 450°C (d), Cu 450°C (e), and NH<sub>4</sub> 450°C (f).

heating at 450°C. Consequently, no substantial alteration of the octahedral sheet occurred due to the H<sup>+</sup> that was generated from the heated NH<sub>4</sub><sup>+</sup>, as is often the case for acid-activated montmorillonites (Madejová *et al.*, 1998).

The intensity change and shift to higher frequency of the Si–O–Al band near 700 cm<sup>-1</sup> may confirm the movement of Cu into the octahedral sites, rather like a mode observed for Cu-muscovite (Friedrich, 2004). However, a discussion about this region in the FTIR spectra (Figure 2) is difficult because of the feldspar admixtures in the samples. Nevertheless, a small shoulder at 500 cm<sup>-1</sup>, appearing after heating at 450°C, can be assigned to Si–O vibration of Cu–O–Si also present in the spectrum of chrysocolla, a Cu silicate (Kelm *et al.*, 2001).

**OH-bending region.** The AlAlOH, AlFeOH, and AlMgOH bands in unheated Cu-Na-, and Cu-NH<sub>4</sub> samples were located at the expected frequencies (Farmer, 1974), at 915, 884, and 848 cm<sup>-1</sup>. Migration of Cu<sup>2+</sup> into the hexagonal cavities of the tetrahedral sheet significantly affected the OH-bending vibrations (McBride and Mortland, 1974). Changes in these vibrations upon heating were also consistent with those suggested by Madejová *et al.* (1999, 2006). The AlMgOH band shifted to greater frequencies to overlap with the AlFeOH band, thus broadening the band near 884 cm<sup>-1</sup>. The AlAlOH band also shifted to a greater frequency, 934 cm<sup>-1</sup>. No additional changes in the OH-bending vibrations were observed for the Cu-NH<sub>4</sub> sample. No band was observed near 680 cm<sup>-1</sup> for the CuCuOH-bending vibrations (Kelm, 2001).

**OH-stretching region.** The OH-stretching band at 3400 cm<sup>-1</sup> from FTIR-ATR spectra of the Cu-Na-montmorillonite and Cu-NH<sub>4</sub>-montmorillonite at different temperatures (Figure 4) arose from the hydration shell of the interlayer cations and significantly decreased in intensity upon heating. This is in accord with the thermal development of the OH-deformation band at 1635 cm<sup>-1</sup>. The band at 3622 cm<sup>-1</sup>, corresponding to the vibrations of the octahedral hydroxyl groups (Farmer, 1974), shifted to greater frequency upon heating at 300 and 450°C, ranging from 3633 cm<sup>-1</sup> to 3640 cm<sup>-1</sup> depending on the sample. This shift to greater frequency is evidence for a decrease in layer charge due to the movement of Cu<sup>2+</sup> into the structure. A similar shift to greater frequency was also observed for heated Ni-montmorillonites (Pálková *et al.*, 2003). This may suggest the occurrence of Cu–OH vibrations, indicating an octahedral environment for the fixed Cu<sup>2+</sup> in the heated sample (Mosser *et al.*, 1997; Madejová *et al.*, 1999). Wright *et al.* (1972) observed the appearance of a shoulder at 3670 cm<sup>-1</sup> for homo-ionic NH<sub>4</sub>-forms of dioctahedral clays after thermal activation, resulting from the change of the interlayer cation (NH<sub>4</sub><sup>+</sup> → H<sup>+</sup>). However, this feature was absent in the current

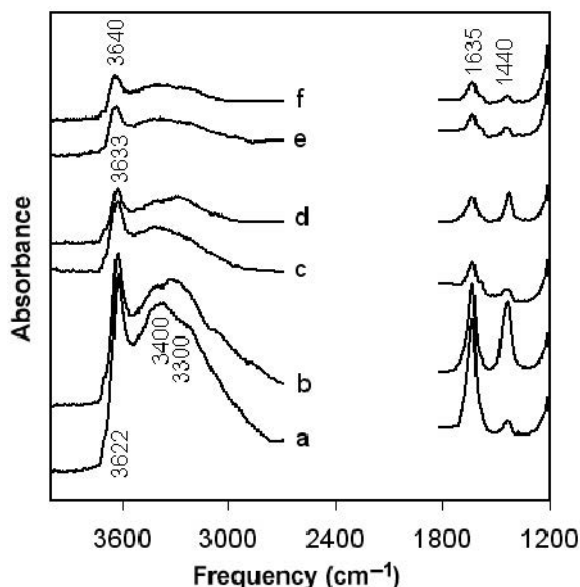


Figure 4. FTIR-ATR spectra of bi-ionic Cu-Na-montmorillonite and Cu-NH<sub>4</sub>-montmorillonite at different temperatures: Cu-Na 60°C (a), Cu-NH<sub>4</sub> 60°C (b), Cu-Na 300°C (c), Cu-NH<sub>4</sub> 300°C (d), Cu-Na 450°C (e), and Cu-NH<sub>4</sub> 450°C (f).

experiments for bi-ionic Cu-NH<sub>4</sub>- or for homo-ionic NH<sub>4</sub>-forms of montmorillonite. This may be because of the relatively small CEC of 60 meq/100 g for the starting material. The possibility that some Cu<sup>2+</sup> was trapped in vacant sites in the octahedral sheet of Cu-NH<sub>4</sub> and Cu-Na samples cannot, however, be ruled out.

**NH vibrations.** The FTIR spectra of the unheated Cu-NH<sub>4</sub> sample showed a broad NH band near 3300 cm<sup>-1</sup> and another near 1440 cm<sup>-1</sup> (Mortland *et al.*, 1963). These bands decreased significantly in intensity after thermal treatment, mirroring the de-ammonization of the interlayer NH<sub>4</sub><sup>+</sup>. The small band near 1440 cm<sup>-1</sup> appearing in the spectrum of the Cu-Na sample probably corresponds to a minor carbonate admixture in the material.

## CONCLUSIONS

Bentonite, a clay containing primarily montmorillonite, has wide potential for environmental application. The purpose of this study was to investigate the migration of Cu<sup>2+</sup> in montmorillonite under moderate, acid, and thermal conditions concerning the fixation of heavy metal cations to bentonite.

(1) The dehydrated Cu<sup>2+</sup> cations migrated into the montmorillonite structure with increasing temperature so that the Cu<sup>2+</sup> was mainly trapped in the hexagonal cavities of the tetrahedral sheet in accordance with previous studies (*e.g.* Madejová *et al.*, 1999, 2006). The possibility remains, however, that some Cu<sup>2+</sup> was trapped in vacant sites in the octahedral sheet after the

heat treatment of the Cu-Na and Cu-NH<sub>4</sub> forms.

(2) In the case of the homo-ionic NH<sub>4</sub> and bi-ionic Cu-NH<sub>4</sub> forms, the structure of the montmorillonite was not substantially altered by the presence of NH<sub>4</sub><sup>+</sup> and heating (NH<sub>4</sub><sup>+</sup> → H<sup>+</sup>), contrary to usual acid activation with strong mineral acids.

(3) De-ammonization certainly led to a decrease in the basal spacing of montmorillonite, but the *d*<sub>001</sub> values did not decrease to <10 Å as was the case for the heated Cu form and Cu-Na sample.

(4) No other effects of the presence of NH<sub>4</sub><sup>+</sup> on the Cu<sup>2+</sup> fixation in the montmorillonite studied here were observed.

## ACKNOWLEDGMENTS

The authors thank Dr K. Emmerich for her cooperation during the course of this work. Dr P. Komadel and an anonymous reviewer are acknowledged for their helpful critical comments.

## REFERENCES

- Barrer, R.M. (1949) Preparation of some crystalline hydrogen zeolites. *Nature (London)*, **164**, 112–113.
- Chitnis, S.R. and Sharma, M.M. (1997) Industrial applications of acid-treated clays as catalysts. *Reactive & Functional Polymers*, **32**, 93–115.
- Emmerich, K. (2000) Die geotechnische Bedeutung des Dehydroxylierungsverhaltens quellfähiger Tonminerale. PhD thesis, ETH Zurich, Switzerland, 143 pp.
- Farmer, V.C. (1974) The layer silicates. Pp. 331–363 in: *The Infrared Spectra of Minerals* (V.C. Farmer, editor). Monograph 4, Mineralogical Society, London.
- Friedrich, F. (2004) Spectroscopic investigations of delaminated and intercalated phyllosilicates. PhD thesis, Universität Karlsruhe, Germany, 146 pp.
- Greene-Kelly, R. (1952) Irreversible dehydration in montmorillonite. *Clay Minerals Bulletin*, **1**, 221–227.
- He, H.P., Guo, J.G., Xie, X.D., and Peng, J.L. (2001) Location and migration of cations in Cu<sup>2+</sup>-adsorbed montmorillonite. *Environment International*, **26**, 347–352.
- Heller-Kallai, L. and Mosser, C. (1995) Migration of Cu ions in Cu montmorillonite heated with and without alkali halides. *Clays and Clay Minerals*, **43**, 738–743.
- Hofmann, U. and Klemen, R. (1950) Verlust der Austauschfähigkeit von Lithiumionen an Bentonit durch Erhitzung. *Zeitschrift für Anorganische Chemie*, **262**, 95–99.
- Karakassides, M.A., Madejová, J., Arvaiová, B., Bourlinos, A., Petridis, D., and Komadel, P. (1999) Location of Li(I), Cu(II) and Cd(II) in heated montmorillonite: evidence from specular reflectance infrared and electron spin resonance spectroscopies. *Journal of Materials Chemistry*, **9**, 1553–1558.
- Karmous, M.S., Ben Rhaïem, H., Naamen, S., Oueslati, W., and Ben Haj Amara, A. (2006) The interlayer structure and thermal behavior of Cu and Ni montmorillonites. *Zeitschrift für Kristallographie, Supplement*, **23**, 431–436.
- Kaufhold, S. and Decher, A. (2003) Natural acidic bentonites from the island of Milos, Greece. *Zeitschrift für Angewandte Geologie*, **49**, 7–12.
- Kelm, U., Sanhueza, V., Madejová, J., Šuchá, V., and Elsass, F. (2001) Evaluation of identification methods for chrysocolla – a Cu-smectite-like hydrous silicate: implications for heap-leaching extraction of copper. *Geologica Carpathica*,

- 52, 111–121.
- Komadel, P. (2003) Chemically modified smectites. *Clay Minerals*, **38**, 127–138.
- Komadel, P., Madejová, J., and Bujdák, J. (2005) Preparation and properties of reduced-charge smectites – a review. *Clays and Clay Minerals*, **53**, 313–334.
- Madejová, J., Bujdák, J., Janek, M., and Komadel, P. (1998) Comparative FT-IR study of structural modifications during acid treatment of dioctahedral smectites and hectorite. *Spectrochimica Acta Part A*, **54**, 1397–1406.
- Madejová, J., Arvaiová, B., and Komadel, P. (1999) FTIR spectroscopic characterization of thermally treated Cu<sup>2+</sup>, Cd<sup>2+</sup>, and Li<sup>+</sup> montmorillonites. *Spectrochimica Acta Part A*, **55**, 2467–2476.
- Madejová, J., Pálková, H., and Komadel, P. (2006) Behaviour of Li<sup>+</sup> and Cu<sup>2+</sup> in heated montmorillonite: Evidence from far-, mid-, and near-IR regions. *Vibrational Spectroscopy*, **40**, 80–88.
- McBride, M.B. and Mortland, M.M. (1974) Copper (II) interactions with montmorillonite: evidence from physical methods. *Soil Science Society of America Proceedings*, **38**, 408–415.
- Mehra, O.P. and Jackson, M.L. (1960) Iron oxide removal from soils and clays by a dithionite-citrate-system buffered with sodium bicarbonate. *Proceedings of the 7th National Conference on Clays and Clay Minerals*, Washington, D.C., pp. 317–327.
- Mortland, M.M., Fripiat, J.J., Chaussidon, J., and Uytterhoeven, J. (1963) Interaction between ammonia and the expanding lattices of montmorillonite and vermiculite. *The Journal of Physical Chemistry*, **67**, 248–258.
- Mosser, C., Michot, L.J., Villieras, F., and Romeo, M. (1997) Migration of cations in copper(II)-exchanged montmorillonite and laponite upon heating. *Clays and Clay Minerals*, **45**, 789–802.
- Oueslati, W., Ben Rhaïem, H., Karmous, M.S., Naaman, S., and Ben Haj Amara, A. (2006) Study of the structural evolution and selectivity of Wyoming montmorillonite in relation with concentration of Cu<sup>2+</sup> and Ni<sup>2+</sup>. *Zeitschrift für Kristallographie, Supplement*, **23**, 425–429.
- Pálková, H., Madejová, J., and Righi, D. (2003) Acid dissolution of reduced-charge Li- and Ni-montmorillonites. *Clays and Clay Minerals*, **51**, 133–142.
- Pérez-Maqueda, L.A., Jiménez de Haro, M.C., Poyato, J., and Pérez-Rodríguez, J.L. (2003) Ammonia release on heating of mechanically treated vermiculite saturated subsequently with ammonium. *Journal of Thermal Analysis and Calorimetry*, **71**, 809–820.
- Pérez-Rodríguez, J.L., Poyato, J., Jiménez de Haro, M.C., Pérez-Maqueda, L.A., and Lerf, A. (2004) Thermal decomposition of NH<sub>4</sub><sup>+</sup>-vermiculite from Santa Olalla (Huelva, Spain) and its relation to the metal ion distribution in the octahedral sheet. *Physics and Chemistry of Minerals*, **31**, 415–420.
- Poyato, J., Pérez-Maqueda, L.A., Jimenez de Haro, M.C., Pérez-Rodríguez, J.L., Šubrt, J., and Balek, V. (2002) Effect of Na<sup>+</sup> and NH<sub>4</sub><sup>+</sup> cations on microstructure changes of natural vermiculite during heat treatment. *Journal of Thermal Analysis and Calorimetry*, **67**, 73–82.
- Seiffarth, T. and Kaps, Ch. (2005) Fixierung von Cu<sup>2+</sup> bei der thermischen Behandlung von (NH<sub>4</sub><sup>+</sup>, Cu<sup>2+</sup>)-ausgetauschten Bentoniten. *Berichte der Deutschen Ton- und Tonmineralgruppe e.V.*, **11**, 93–96.
- Shaïek, M., Karmous, M.S., Naamen, S., Ben Rhaïem, H., Ben Haj Amara, A., and Plançon, A. (2003) Structural evolution of the heated dioctahedral montmorillonite saturated by Cu<sup>2+</sup>, Ni<sup>2+</sup> and Cs<sup>+</sup>. *Abstracts of the 10th Conference of the European Clay Groups Association, Euroclay 2003*, Modena, p. 258.
- Tettenhorst, R. (1962) Cation migration in montmorillonites. *American Mineralogist*, **47**, 769–773.
- Tributh, H. and Lagaly, G. (1986) Aufbereitung und Identifizierung von Boden- und Lagerstättentonen. I. Aufbereitung der Proben im Labor. *GIT Fachzeitschrift für das Laboratorium*, **30**, 524–529.
- Wolters, F. (2005) Classification of montmorillonites. PhD thesis, Universität Karlsruhe, Germany, 98 pp.
- Wolters, F. and Emmerich, K. (2007) Thermal reactions of smectites – Relation of dehydroxylation temperature to octahedral structure. *Thermochimica Acta*, **462**, 80–88.
- Wright, A.C., Granquist, W.T., and Kennedy, J.V. (1972) Catalysis by layer lattice silicates. I. The structure and thermal modification of a synthetic ammonium dioctahedral clay. *Journal of Catalysis*, **25**, 65–80.

(Received 2 October 2007; revised 10 October 2008; Ms. 0081; A.E. P. Komadel)