

Hydroxylbastnäsité-(La), an “old new” bastnäsité-group mineral

Igor V. Pekov^{1*}, Natalia V. Zubkova¹, Anatoly V. Kasatkin², Nikita V. Chukanov³, Natalia N. Koshlyakova¹, Dmitry A. Ksenofontov¹, Radek Škoda⁴, Sergey N. Britvin⁵, Anatoly S. Kirillov⁵, Anatoly N. Zaitsev⁵, Aleksey M. Kuznetsov⁶ and Dmitry Yu. Pushcharovsky¹

¹Faculty of Geology, Moscow State University, Vorobievyy Gory, 119991 Moscow, Russia

²Fersman Mineralogical Museum of the Russian Academy of Sciences, Leninsky Prospekt 18-2, 119071 Moscow, Russia

³Federal Research Center of Problems of Chemical Physics and Medicinal Chemistry of the Russian Academy of Sciences, 142432 Chernogolovka, Moscow region, Russia

⁴Department of Geological Sciences, Faculty of Science, Masaryk University, Kotlářská 2, 611 37, Brno, Czech Republic

⁵St. Petersburg State University, University Emb. 7/9, 199034 St. Petersburg, Russia

⁶Oktyabrskaya str., 5-337, 454071 Chelyabinsk, Russia

*E-mail: igorpekov@mail.ru

Running title: Hydroxylbastnäsité-(La), a new mineral

Abstract

Hydroxylbastnäsité-(La), the OH- and La-dominant member of the bastnäsité group, known in fact for many years, was studied in detail and has been approved by the IMA-CNMNC as a new mineral species with the ideal, end-member formula $\text{La}(\text{CO}_3)(\text{OH})$. The holotype originates from the Vuoriyarvi (another spelling: Vuorijärvi) alkaline-ultrabasic complex, Northern Karelia, and the cotype from the Mochalin Log *REE* deposit, Potaniny Mts, South Urals, both Russia. At Vuoriyarvi, hydroxylbastnäsité-(La) occurs as clusters (up to 1 mm) of light brown, honey-yellow or colourless hexagonal tabular to short-prismatic crystals up to 0.15 mm associated with fluorite and ancylite-(Ce) in cavities of calcite-dolomite carbonatites. At Mochalin Log,



Mineralogical Society

This is a 'preproof' accepted article for Mineralogical Magazine. This version may be subject to change during the production process.

DOI: 10.1180/mgm.2024.65

hydroxylbastnäsite-(La) forms light brown grains up to 0.2 mm included in massive aggregates of other *LREE* minerals: bastnäsite-(Ce), bastnäsite-(La), percleveite-(Ce), percleveite-(La), biraite-(Ce), biraite-(La), törnebohmit-(La), ferriperbøite-(Ce), allanite-(Ce), *etc.* D_{meas} is 4.75(2), D_{calc} is 4.778 g cm⁻³ (holotype). Hydroxylbastnäsite-(La) is optically uniaxial (+), $\omega = 1.76(1)$, $\varepsilon = 1.86(1)$ (holotype). The chemical composition (wt.%, electron microprobe, CO₂ and H₂O calculated: holotype/cotype) is: CaO 0.23/0.00, SrO 0.07/0.00, La₂O₃ 39.47/39.58, Ce₂O₃ 33.51/31.99, Pr₂O₃ 1.03/1.51, Nd₂O₃ 1.95/2.38, F 0.76/3.33, CO₂ 20.49/20.34, H₂O 3.77/2.58, –O=F 0.32/1.40, total 100.96/100.31. The empirical formulae, calculated based on the sum of metal cations of 1 *apfu* and one CO₃ group *pfu*, are (La_{0.52}Ce_{0.44}Nd_{0.02}Pr_{0.01}Ca_{0.01})_{Σ1.00}(CO₃)[(OH)_{0.90}F_{0.09}]_{Σ0.99} (holotype) and (La_{0.53}Ce_{0.42}Nd_{0.03}Pr_{0.02})_{Σ1}(CO₃)[(OH)_{0.62}F_{0.38}]_{Σ1.00} (cotype). Hydroxylbastnäsite-(La) is hexagonal, *P*-6, unit-cell parameters (from powder XRD data, holotype/cotype) are: *a* 12.537(3)/12.533(1), *c* 9.968(2)/9.908(1) Å, *V* 1356.8(5)/1347.9(3) Å³ and *Z* = 18. Strong reflections of the powder XRD pattern [*d*, Å(*I*)(*hkl*)] are (holotype): 4.98(39)(002), 3.616(88)(300), 2.926(100)(302), 2.089(41)(330), 2.052(46)(304) and 1.927(40)(332). The crystal structure of holotype hydroxylbastnäsite-(La) was refined by the Rietveld method, $R_{\text{wp}} = 0.0071$, $R_{\text{p}} = 0.0050$, $R_{\text{obs}} = 0.0466$. It is isostructural to hydroxylbastnäsite-(Ce) and synthetic bastnäsite-type hydroxyl-carbonates $REE^{3+}(\text{CO}_3)(\text{OH})$ ($REE = \text{La-Er}$), but differs from fluorine-dominant bastnäsites which adopt the space group *P*-62*c*.

Keywords: hydroxylbastnäsite-(La); new mineral; bastnäsite group; rare-earth carbonate; crystal structure; Vuoriyarvi complex; Mochalin Log *REE* deposit.

Introduction

The minerals of the bastnäsite group (hereafter bastnäsites) are carbonates of rare-earth elements (*REE*) with the general formula $REE^{3+}(\text{CO}_3)X^-$ in which species-defining $REE = \text{La, Ce, Nd, or Y}$ and $X = \text{F or OH}$. The root names of F-dominant members are based on the term 'bastnäsite' while OH-dominant members on the term 'hydroxylbastnäsite', and the Levinson's modifier indicates the prevailing *REE*. Bastnäsite-(Ce), ideally Ce(CO₃)F, is one of the most widespread rare-earth minerals, an important (in some deposits the major) ore mineral of *REE*. It is known

for two centuries being first described by Berzelius (1825) as *Basisk flusspatssyradt Cerium*. Other members of the group were defined as individual, valid mineral species since the 1960s, *i.e.* after the establishing of the IMA Commission on New Minerals and Mineral Names in 1959: they are hydroxylbastnäsite-(Ce) (Kirillov, 1964), bastnäsite-(La) (Levinson, 1966), bastnäsite-(Y) (Mineev *et al.*, 1970), hydroxylbastnäsite-(Nd) (Maksimović and Pantó, 1985), bastnäsite-(Nd) (Miyawaki *et al.*, 2013), and the described in the present paper hydroxylbastnäsite-(La) (Pekov *et al.*, 2021). It should be noted that the histories of the definition of hydroxylbastnäsite-(Ce), bastnäsite-(La), bastnäsite-(Y), and hydroxylbastnäsite-(La) as mineral species are not very simple; for the three formers, the historical overview is reported by (Pekov, 1998) while for hydroxylbastnäsite-(La), which is first described as a valid mineral species in the present paper, it is given in the next paragraph.

Hydroxylbastnäsite-(La) is in fact "an old new" mineral. Probably the first recorded locality for this mineral species is the Mochalin Log *REE* deposit in South Urals, Russia. A bastnäsite-group mineral was first described from Mochalin Log in 1861 by Fedor Korovaev as "kyshtymoparisite", or "Kischtim-Parisit" (Korovaev, 1861; Korovaeff, 1862); some later this name was modified as "kischtimite" by Brush (1863). In 20th century, the mineral from Mochalin Log was systematically studied and reported as bastnäsite by Lacroix (1912), Silberminz (1929), Alimarin (1930) and Svyazhin (1965). Bastnäsite chemically analyzed by Alimarin was La-rich and contained 2.24 wt.% F and 1.83 wt.% H₂O (Alimarin, 1930) that corresponds to the OH/(OH+F) ratio equal to 0.63. Based on these data, Strunz (1962) concluded that "*kischtimite is bastnäsite with OH instead of F and relatively high La content*". Svyazhin (1965) found that bastnäsite from Mochalin Log contains comparable amounts of Ce and La and also suggested to preserve the name "kyshtymite" (as modified "kischtimite", in accordance with common English transliteration of Russian geographical names) for a La-rich and F-depleted variety of bastnäsite. The first quantitative electron-microprobe analyses of bastnäsite-group minerals from Mochalin Log were published by us in 2002: bastnäsite-(Ce), bastnäsite-(La), hydroxylbastnäsite-(Ce) and a potential mineral species "hydroxylbastnäsite-(La)" were identified here (Pekov *et al.*, 2002). The latter mineral was also found at several other localities. Chemical data for its supergene Ce-depleted variety from bauxite deposits of Hungary, Greece and the former Yugoslavia were reported by Maksimović and Pantó (1983) and Pantó and Maksimović (2001) (see also: Hawthorne *et al.*, 1986; Jambor and Roberts, 2002). The mineral chemically corresponding to

hydroxylbastnäsite-(La) was reported from rhyolites near Tisovec-Rejkovo, Slovakia (Ondrejka *et al.*, 2005).

However, despite use of the name "hydroxylbastnäsite-(La)" in literature and databases, the natural OH- and La-dominant member of the bastnäsite group was not studied in detail and had never been formally accepted by the IMA as valid mineral species. To fill this lacuna, we examined hydroxylbastnäsite-(La) on the specimens from two localities and submitted the proposal on this mineral as a new species to the IMA Commission on New Minerals, Nomenclature and Classification (CNMNC). The specimen considered as the holotype (most studied) originates from the Vuoriyarvi (another spelling: Vuorijärvi) alkaline-ultrabasic complex, Northern (Polar) Karelia (near the border with Kola Peninsula), Murmansk Oblast, Russia. The cotype material originates from the Mochalin Log *REE* deposit located in the valley of the Mochalin Log stream, a left tributary of the Borzovka river, in Potaniny Mts, 14 km N of the city of Kyshtym, Chelyabinsk Oblast', South Urals, Russia. Note, both these localities are also the co-type localities of hydroxylbastnäsite-(Ce) (see Pekov, 1998).

Both the mineral and its name, obvious for OH- and La-dominant member of the bastnäsite group, have been approved by the IMA-CNMNC, IMA2021-001 (Pekov *et al.*, 2021). The type specimens of hydroxylbastnäsite-(La) are deposited in the systematic collection of the Fersman Mineralogical Museum of the Russian Academy of Sciences, Moscow, Russia with the catalogue numbers 97514 (holotype material from Vuoriyarvi) and 97515 (cotype from Mochalin Log). The symbol for this mineral is Hbsn-La (Warr, 2021; updated March 2023 version at <http://cnmnc.units.it/>).

Occurrence and general appearance

At the Vuoriyarvi alkaline-ultrabasic complex (for its description see e.g.: Kukharensky *et al.*, 1965; Karchevsky and Moutte, 2004 and references therein), hydroxylbastnäsite-(La) was identified in the material collected by one of the authors (A.S.K.) in the late 1950s. This mineral forms well-shaped hexagonal tabular to short-prismatic crystals up to 0.15 mm in size. The pinacoid {001} and the hexagonal prism {100} are their main forms, the narrow faces {103} and {201} were observed on some crystals. The crystals are typically combined in dense, sometimes spherical clusters (Fig. 1) up to 1 mm across. Some crystals completely consist of hydroxylbastnäsite-(La) whereas the others contain a core composed by hydroxylbastnäsite-(Ce),

with $Ce > La$. Hydroxylbastnäsites together with fluorite and ancylite-(Ce) occur in cavities of calcite-dolomite carbonatites. We consider this mineral assemblage as formed during a late, low-temperature hydrothermal stage of the carbonatite evolution.

Mochalin Log is a classic, historical locality of Ce- and La-dominant bastnäsites including the hydroxyl-prevailing species (Korovaev, 1861; Korovaeff, 1862; Silberminz, 1929; Alimarin, 1930; Svyazhin, 1965; Pekov *et al.*, 2002). They belong here to the rich and diverse assemblage of light *REE* (*LREE*) minerals which has contact metasomatic origin. Most probably, it was formed during the fenitization of granitic pegmatites located within granite-gneisses in the southern exocontact zone of the Vishnevogorskiy alkaline intrusive complex mainly consisting of syenites and miaskites. For the general data on the Mochalin Log deposit see recent summarizing paper (Kasatkin *et al.*, 2020) and references therein. At Mochalin Log, hydroxylbastnäsite-(La) occurs as anhedral grains up to 0.1×0.2 mm included in massive aggregates of other *LREE* minerals (Fig. 2). In different samples, it is associated with bastnäsite-(Ce), bastnäsite-(La), percleveite-(Ce), percleveite-(La), biraite-(Ce), biraite-(La), törnebohmite-(La), ferriperbøeite-(Ce), allanite-(Ce), allanite-(La), ferriallanite-(La), alexkuznetsovite-(Ce), alexkuznetsovite-(La), perrierite-(Ce), perrierite-(La), fluorbritholite-(Ce), stillwellite-(Ce), thorianite, and quartz.

Physical properties and optical data

Hydroxylbastnäsite-(La) from both type localities is transparent to translucent and typically has light brown colour. Some crystals from Vuoriyarvi are light honey-yellow or colourless. The streak is white. The lustre is strong vitreous on crystal faces and greasy on broken surface. The mineral is brittle, no cleavage or parting was observed. The fracture is uneven. The Mohs hardness is *ca.* 4. The density, measured by microvolumetric method for the holotype, is $4.75(2)$ g cm^{-3} . The density calculated for the holotype using the empirical formula and unit-cell volume found from powder X-ray diffraction (XRD) data is 4.778 g cm^{-3} .

Optical data were obtained for the holotype specimen. Hydroxylbastnäsite-(La) is optically uniaxial (+), $\omega = 1.76(1)$, $\epsilon = 1.86(1)$ (589 nm). In plane polarized transmitted light, it is colourless and non-pleochroic.

Infrared spectroscopy

In order to obtain an infrared (IR) absorption spectrum, powdered sample of the holotype hydroxylbastnäsite-(La) (curve *a* in Fig. 3) was mixed with anhydrous KBr, pelletized, and analyzed using an ALPHA FTIR spectrometer (Bruker Optics) at a resolution of 4 cm⁻¹. A total of 16 scans were accumulated. The IR spectrum of an analogous pellet of pure KBr was used as a reference. The typical sample of bastnäsite-(Ce) involved for comparison (curve *b* in Fig. 3) was prepared and studied using the same procedures.

The assignment of absorption bands observed in different wavenumber ranges is as follows.

3400–3700 cm⁻¹ – O–H stretching vibrations.

1400–1500 cm⁻¹ – degenerate asymmetric stretching vibrations of (CO₃)²⁻.

1080–1100 cm⁻¹ – nondegenerate symmetric stretching vibrations of (CO₃)²⁻.

840–880 cm⁻¹ – out-of-plane bending vibrations of (CO₃)²⁻ (a nondegenerate mode).

781 – *LREE*···O–H in-plane bending vibrations (broad band, possibly, superposition of several bands).

680–730 cm⁻¹ – in-plane bending vibrations of (CO₃)²⁻ (a degenerate mode).

599 cm⁻¹ – *LREE*···O–H out-of-plane bending vibrations (rotation around the *LREE*···O ionic bond) – broad band, possibly, superposition of several bands.

Below 500 cm⁻¹ – lattice modes involving *LREE*···O and (CO₃)²⁻ librational vibrations.

The intrinsic fundamental modes of the (CO₃)²⁻ and (OH)⁻ anions were assigned in accordance with Nakamoto (2008).

The remaining absorption bands with maxima at 599 and 781 cm⁻¹ were assigned by analogy with numerous oxysalts with additional (OH)⁻ anions in which *M*···O–H bending vibrations are usually observed in the range of 580 – 830 cm⁻¹ (see the reference books Chukanov and Chervonnyi, 2016; Chukanov and Viggasina, 2020 and references therein). It is to be noted that in the IR spectra of F-dominant members of the bastnäsite group these bands are absent or are very weak.

Weak bands in the range of 1700–1500 cm⁻¹ correspond to overtones and combination modes.

The IR spectrum of hydroxylbastnäsite-(La) differs from that of bastnäsite-(Ce) by the presence of multiple bands of O–H stretching vibrations and *LREE*···O–H bending and libration bands as well as splitting of all bands related to the (CO₃)²⁻ groups. The band of nondegenerate symmetric stretching vibrations of (CO₃)²⁻ (*i.e.* mode which would be inactive in the IR spectrum of

a mineral with undistorted CO₃ triangles) at 1082 with the shoulder at 1091 cm⁻¹ as well as splitting of the nondegenerate band of out-of-plane bending vibrations of (CO₃)²⁻ indicate the presence of non-equivalent distorted CO₃ triangles in the structure of hydroxylbastnäsite-(La).

Four bands in the O–H stretching region correspond to at least four non-equivalent OH groups, but taking into account asymmetry of the bands at 3472 and 3563, one can suppose that the number of non-equivalent OH groups is > 4.

Chemical composition

The chemical composition of hydroxylbastnäsite-(La) was studied by electron microprobe in two laboratories. The holotype was investigated in the Laboratory of Analytical Techniques of High Spatial Resolution, Department of Petrology, Moscow State University, using a Jeol JSM-6480LV scanning electron microscope equipped with an INCA-Wave 500 wavelength-dispersive spectrometer, with an acceleration voltage of 20 kV and a beam current of 10 nA; the electron beam was rastered to the 5 × 5 μm² area. The cotype was analyzed in the Laboratory of Electron Microscopy and Microanalysis, Department of Geological Sciences, Masaryk University, Brno, using a Cameca SX-100 electron microprobe (WDS mode, acceleration voltage of 15 kV, a beam current of 10 nA, and a 5 μm beam diameter). The chemical data in wt.% are given in Table 1, as well as the probe standards. Contents of other elements with atomic numbers > 4 were below detection limits. The special attention was paid to the correctness of quantitative determination of fluorine due to overlap of *K* line of F with *M* line of Ce.

The amounts of H₂O and CO₂ could not be determined directly because of the paucity of pure material. The presence of both (CO₃)²⁻ and (OH)⁻ groups as species-defining constituents in hydroxylbastnäsite-(La) is undoubtedly shown by the crystal structure data (see below) and the IR spectrum. The presence of (CO₃)²⁻ (as in all other bastnäsite-group carbonates) is also confirmed by the common chemical test: the mineral dissolves in warm HCl aqueous solution or in cold dilute H₂SO₄ with effervescence (CO₂ gas bubbling release).

The empirical formulae, calculated on the basis of the sum of metal cations of one atom per formula unit (*apfu*) and one CO₃ group *pfu*, are as follows:

holotype (Vuoriyarvi): (La_{0.52}Ce_{0.44}Nd_{0.02}Pr_{0.01}Ca_{0.01})_{Σ1.00}(CO₃)[(OH)_{0.90}F_{0.09}]_{Σ0.99};

cotype (Mochalin Log): (La_{0.53}Ce_{0.42}Nd_{0.03}Pr_{0.02})_{Σ1.00}(CO₃)[(OH)_{0.62}F_{0.38}]_{Σ1.00}.

The simplified formula is $(\text{La,Ce})(\text{CO}_3)(\text{OH,F})$. The idealised, end-member formula is $\text{La}(\text{CO}_3)(\text{OH})$ which requires La_2O_3 75.45, CO_2 20.38, H_2O 4.17, total 100 wt.%.

The values of the Gladstone–Dale compatibility index $1 - (\text{K}_p/\text{K}_c)$ (Mandarino, 1981) for the holotype hydroxylbastnäsité-(La) calculated with D_{meas} and D_{calc} are -0.009 and -0.003 , respectively (both rated as superior).

X-ray crystallography and crystal structure determination details

Single-crystal XRD studies of the holotype sample of hydroxylbastnäsité-(La) were carried out at room temperature using an Xcalibur S diffractometer equipped with a CCD detector ($\text{MoK}\alpha$ -radiation). The mineral is hexagonal, $a = 12.562(2)$, $c = 10.015(2)$ Å and $V = 1368(1)$ Å³.

Powder XRD data for both holotype and cotype samples were collected with a Rigaku R-Axis Rapid II single-crystal diffractometer equipped with cylindrical image plate detector (radius 127.4 mm) using Debye-Scherrer geometry, $\text{CoK}\alpha$ radiation (rotating anode with VariMAX microfocussing optics), 40 kV, 15 mA, and exposure 15 min. Angular resolution of the detector is 0.045° (2θ ; pixel size 0.1 mm). The data were integrated using the software package Osc2Tab (Britvin *et al.*, 2017). Powder XRD data for the holotype are given in Table 2, the powder XRD pattern of the cotype shows no significant differences. The hexagonal unit cell parameters calculated from powder data for holotype / cotype are: $a = 12.537(3) / 12.533(1)$, $c = 9.968(2) / 9.908(1)$ Å, $V = 1356.8(5) / 1347.9(3)$ Å³ and $Z = 18$.

All tested single crystals of hydroxylbastnäsité-(La) demonstrated not very high quality: even they looked to be perfect (Fig. 1), they have in fact mosaic character in the inner structure and consist of blocks slightly disoriented with respect to each other. The crystal structure of holotype hydroxylbastnäsité-(La) was refined with the powder XRD data (for the data collecting details see above) using the Rietveld method. Data treatment and the Rietveld structure analysis were carried out using JANA2006 program package (Petříček *et al.*, 2006). The structure model of hydroxylbastnäsité-(Ce) (Yang *et al.*, 2008) was taken as the starting one. Scattering curve of Ce was used for the REE sites. The profiles were modeled using a pseudo-Voigt function. The structure was refined in isotropic approximation of atomic displacements, the values of U_{iso} for all atoms of each sort were restricted to be equal, atomic coordinates and U_{iso} of C atoms were fixed on the last stages of the refinement. The cation-anion interatomic distances were restricted nearby the values of the starting structure model. The space group is $P-6$, for the refined unit-cell

parameters see above. Final agreement factors are: $R_{wp} = 0.0071$, $R_p = 0.0050$, $R_{obs} = 0.0466$. The observed and calculated powder XRD diagrams demonstrate a very good agreement (Fig. 4). Coordinates and displacement parameters of atoms are given in Table 3 and selected interatomic distances in Table 4.

Discussion

Fluorine- and hydroxyl-dominant members of the bastnäsite group are structurally close but not isostructural. Fluorine-dominant minerals of the bastnäsite-(Ce) – bastnäsite-(La) series and bastnäsite-(Nd) adopt the space group $P-62c$ and are characterized by a unit cell with the following parameters: $a = 7.1\text{--}7.2$, $c = 9.7\text{--}9.8$ Å and $V = 422\text{--}436$ Å³ ($Z = 6$) (Ofstedal, 1931; Donnay and Donnay, 1953; Ni *et al.*, 1993; Terada *et al.*, 1993; Mi *et al.*, 1996; Miyawaki *et al.*, 2013). The crystal structure of bastnäsite-(Y) was not studied. Among hydroxyl-dominant minerals of the group, only hydroxylbastnäsite-(Ce) was structurally studied earlier, on samples from Trimouns, Luzenac, France and Kamihouri, Miyazaki Prefecture, Japan. It crystallizes in the space group $P-6$ and has a unit cell with the following parameters: $a = 12.41\text{--}12.47$, $c = 9.85\text{--}9.96$ Å and $V = 1314\text{--}1342$ Å³ ($Z = 18$) (Yang *et al.*, 2008; Michiba *et al.*, 2013); see Table 5. Synthetic bastnäsite-like hydroxyl-carbonates $REE^{3+}(\text{CO}_3)(\text{OH})$ with $REE = \text{La, Pr, Nd, Sm, Eu, Gd, Tb, Dy, Ho, and Er}$ demonstrate the same space group $P-6$ and unit-cell metrics as hydroxylbastnäsite-(Ce) (Christensen, 1973; Kutlu and Meyer, 1999; Michiba *et al.*, 2011). Note, synthetic bastnäsite-like $\text{La}(\text{CO}_3)(\text{OH})$, an analogue of the end-member hydroxylbastnäsite-(La) is known (Hsu *et al.*, 1992; Michiba *et al.*, 2011). The relationship between unit cells of F- and OH-dominant bastnäsites is as follows: $a_{\text{hydroxylbastnäsite}} \approx a_{\text{bastnäsite}}\sqrt{3}$, $c_{\text{hydroxylbastnäsite}} \approx c_{\text{bastnäsite}}$. The difference between F- and OH-dominant bastnäsites is in atomic arrangement (Figs. 5 and 6). In particular, there are 6, 3, and 5 symmetrically non-equivalent CO_3 groups, REE^{3+} cations, and X^- anions, respectively, in hydroxylbastnäsites as distinct to 1, 1, and 2 ones in F-dominant bastnäsites (see references above). However, the crystal structures of the bastnäsite-like compounds crystallized in the space groups $P-6$ and $P-62c$ exhibit many common features: they are based on the layers of REE and F/OH alternating with the layers of CO_3 groups (Fig. 6).

As our data show, hydroxylbastnäsite-(La) is isostructural to hydroxylbastnäsite-(Ce) (Yang *et al.*, 2008; Michiba *et al.*, 2013) and synthetic bastnäsite-like hydroxyl-carbonates $REE^{3+}(\text{CO}_3)(\text{OH})$ with $REE = \text{La–Er}$ (Michiba *et al.*, 2011 and references therein) rather than F-

dominant bastnäsites. The crystal structure of hydroxylbastnäsite-(La) (Fig. 5a) is based upon the (001) layers of REE^{3+} cations and $(OH)^-$ anions interspersed with carbonate layers in a 1:1 ratio. Three crystallographically non-equivalent REE sites occupy nine-fold polyhedra $REEO_6(OH)_3$. Hydroxyl groups are located inside REE layers where REE -centred polyhedra are connected *via* common O–OH edges and OH vertices (Fig. 5b). Neighboring REE layers are connected *via* CO_3 groups and one common O vertex of REE -centred polyhedra. As well as in hydroxylbastnäsite-(Ce), the coordination of REE^{3+} cations is formed by three $(OH)^-$ anions and five $(CO_3)^{2-}$ anions four of which are monodentate ligands and one is a bidentate ligand in contrast with F-dominant bastnäsites crystallizing in space group $P-62c$ where REE sites are coordinated by three F^- anions and six monodentate $(CO_3)^{2-}$ anions. The comparison of the atomic arrangements in the structures of bastnäsite-(Ce) and hydroxylbastnäsite-(La) is given in Fig. 6.

The difference in symmetry causes the difference (not too strong but distinct) in powder XRD patterns of F- and OH-dominant bastnäsites, at the first instance, due to additional systematic absences in the patterns of F-dominant bastnäsites (space group $P-62c$) in comparison with the patterns of hydroxylbastnäsites ($P-6$). The powder XRD pattern of hydroxylbastnäsite-(La) (Table 2) shows the similarity with the calculated pattern of $REE^{3+}(CO_3)(OH)$ with the space group $P-6$. In particular, hydroxylbastnäsite-(La) demonstrates three reflections in the region 2.7 – 2.5 Å in which the calculated powder XRD pattern of hydroxylbastnäsites ($P-6$) also contains three reflections with $I \geq 0.5\%$, whereas the calculated pattern of F-dominant bastnäsites ($P-62c$) contains only one reflection. A distinct reflection with $d = 2.235$ Å is present in both measured and calculated powder XRD patterns of hydroxylbastnäsite-(La) but is absent in the patterns of F-dominant bastnäsites ($P-62c$). These and some other features of the powder XRD pattern causes the choice of the space group $P-6$ and corresponding unit-cell metrics for hydroxylbastnäsite-(La).

The IR spectrum of hydroxylbastnäsite-(La) (curve **a** in Fig. 3), unlike the IR spectra of F-dominant bastnäsite-group minerals (see, *e.g.*, curve **b** in Fig. 3), clearly demonstrates the presence of several non-equivalent $(CO_3)^{2-}$ and $(OH)^-$ groups (see above) that confirms its lower symmetry in comparison with F-dominant bastnäsites.

Hydroxylbastnäsite-(La) and hydroxylbastnäsite-(Ce) have distinctly higher values of unit-cell dimensions and volume (easily comparable in the same setting) and refractive indices in comparison with their F-dominant analogues (Table 5). Triple unit-cell volume of bastnäsite-

(Ce) – bastnäsite-(La) series minerals ($Z = 18$) varies from 1266 to 1308 Å³ whereas minerals of the hydroxylbastnäsite-(Ce) – hydroxylbastnäsite-(La) series have unit-cell volume from 1314 to 1357 Å³. Unit-cell dimensions of two samples of hydroxylbastnäsite-(La), from Vuoriyarvi and Mochalin Log (see above), is in agreement with the OH:F ratio. The refractive indices of hydroxylbastnäsites are higher than corresponding values of F-dominant bastnäsites, with the significant difference of 0.04–0.05 (Table 5). The distinct increase of unit-cell dimensions with the substitution of F⁻ by (OH)⁻ is typical in such pairs of isotypic or structurally close compounds [e.g., the fluorapatite Ca₅(PO₄)₃F – hydroxylapatite Ca₅(PO₄)₃(OH) (White *et al.*, 2005) or fluoborite Mg₃(BO₃)F₃ – hydroxylborite Mg₃(BO₃)(OH)₃ series (Cámara and Ottolini, 2000; Rudnev *et al.*, 2007)], as well as refractive indices. These characteristics can be used as good indicators of the prevailing of F⁻ or (OH)⁻ in rare-earth minerals of the bastnäsite group. The correctness of determination of chemical and crystal data and density of hydroxylbastnäsite-(La) is confirmed by very low (superior) value of the Gladstone-Dale compatibility index.

In terms of end-member compositions, hydroxylbastnäsite-(La) is dimorphous with kozoite-(La), ideally La(CO₃)(OH), a member of the ancylite supergroup (Miyawaki *et al.*, 2003; Wang *et al.*, 2024).

Acknowledgements

We thank three anonymous referees for their valuable comments. The mineralogical and crystal chemical studies of hydroxylbastnäsite-(La) from Vuoriyarvi was performed in accordance with the State Task of the RF No. 121061600049-4. The IR spectra were obtained and interpreted in accordance with the State Task of the RF No. 124013100858-3. Powder XRD study was done at the Center for X-ray Diffraction Studies of the Research Park of St. Petersburg State University within the project No. AAAA-A19-119091190094-6.

References

- Aleksandrov I.V., Ivanov V.I. and Sin'kova L.A. (1965) New data on bastnäsite. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **94**(3), 323–326 [in Russian].
- Alimarin I.P. (1930) On the chemical analysis of bastnäsite – in: “Rare-Earth Minerals of Kyshtym Area”. *Trudy Instituta Prikladnoy Mineralogii (Proceedings of the Institute of Applied Mineralogy)*, **44**, 47–57 [in Russian].

- Anthony J.W., Bideaux R.A., Bladh K.W. and Nichols M.C. (2003) *Handbook of Mineralogy. V. Borates, Carbonates, Sulfates*. Mineral Data Publishing, Tucson, 813 pp.
- Berzelius J.J. (1825) Flusspatzsyradt och kolsyradt cerium. *Årsberättelser om Vetenskapernas Framsteg*. Afgivne af Kongl. Vetenskaps-Academiens Embetsman: 31 Mars 1824, 201–202.
- Britvin S.N., Dolivo-Dobrovolsky D.V. and Krzhizhanovskaya M.G. (2017) Software for processing the X-ray powder diffraction data obtained from the curved image plate detector of Rigaku RAXIS Rapid II diffractometer. *Zapiski Rossiiskogo Mineralogicheskogo Obshchestva*, **146(3)**, 104–107 (in Russian).
- Brush G.J. (1863) Kischtimite, a new mineral. *American Journal of Science*, **35**, 427–428.
- Cámara F. and Ottolini L. (2000) New data on the crystal-chemistry of fluoborite, by means of SREF, SIMS and EMP analysis. *American Mineralogist*, **85**, 103–107.
- Christensen A.N. (1973) Hydrothermal preparation of rare earth hydroxycarbonates. The crystal structure of NdOHCO₃. *Acta Chemica Scandinavica*, **27**, 2973–2982.
- Chukanov N.V. and Chervonnyi A.D. (2016) *Infrared Spectroscopy of Minerals and Related Compounds*. Springer, Cham, 1109 pp.
- Chukanov N.V. and Viggasina M.F. (2020) *Vibrational (Infrared and Raman) Spectra of Minerals and Related Compounds*. Springer, Dordrecht, 1376 pp.
- Donnay G. and Donnay J.D.H. (1953) The crystallography of bastnaesite, parisite, roentgenite and synchysite. *American Mineralogist*, **38**, 932–963.
- Hawthorne F.C., Fleischer M., Grew E.S., Grice J.D., Jambor J.L., Puziewicz J., Roberts A.C., Vanko D.A. and Zilcher J.A. (1986) New mineral names. *American Mineralogist*, **71**, 1277–1282.
- Hsu L.C. (1992) Synthesis and stability of bastnaesites in a part of the system (Ce, La)-F-H-C-O. *Mineralogy and Petrology*, **47**, 81–101.
- Jambor J.L. and Roberts A.C. (2002) New mineral names. *American Mineralogist*, **87**, 765–768.
- Karchevsky P.I. and Moutte J. (2004) The phoscorite-carbonatite complex of Vuoriyarvi, northern Karelia. In: *Phoscorites and Carbonatites from Mantle to Mine: The Key Example of the Kola Alkaline Province* (eds: F. Wall and A.N. Zaitsev). Mineralogical Society Series, **10**. Mineralogical Society, London, 163–199.
- Kasatkin A.V., Zubkova N.V., Pekov I.V., Chukanov N.V., Škoda R., Polekhovskiy Yu.S., Agakhanov A.A., Belakovskiy D.I., Kuznetsov A.M., Britvin S.N. and Pushcharovskiy

- D.Yu. (2020) The mineralogy of the historical Mochalin Log REE deposit, South Urals, Russia. Part I. New gatelite-group minerals ferriperbœite-(La), $(\text{CaLa}_3)(\text{Fe}^{3+}\text{Al}_2\text{Fe}^{2+})[\text{Si}_2\text{O}_7][\text{SiO}_4]_3\text{O}(\text{OH})_2$, and perbœite-(La), $(\text{CaLa}_3)(\text{Al}_3\text{Fe}^{2+})[\text{Si}_2\text{O}_7][\text{SiO}_4]_3\text{O}(\text{OH})_2$. *Mineralogical Magazine*, **84**, 593–607.
- Kirillov A.S. (1964) Hydroxyl bastnäsité, a new variety of bastnäsité. *Doklady Akademii Nauk SSSR, Earth Science Sections*, **159**, 93–95.
- Kirillov A.S. (1966) Hydroxyl-bastnäsité, a new mineral variety. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **95(1)**, 51–59 [in Russian].
- Korovaeff Th. (1862) Der Kischtim-Parisit, ein neues Mineral. *Bulletin de l'Académie Impériale des Sciences de Saint-Pétersbourg*, IV, 401–408.
- Korovaev F. (1861) Kyshtymoparisite, a new mineral. *Gornyi Zhurnal (Mining Journal)*, **4(12)**, 445–454 [in Russian].
- Kukhareno A.A., Orlova M.P., Bulakh A.G., Bagdasarov E.A., Rimskaya-Korsakova O.M., Nefedov E.I., Ilinskiy G.A., Sergeev A.S. and Abakumova N.B. (1965) *The Caledonian Complex of Ultramafic, Alkaline Rocks and Carbonatites of Kola Peninsula and Northern Karelia*. Nedra Publishing, Leningrad, 772 pp. (in Russian).
- Kupriyanova I.I. (1968) Bastnäsité from albitites. *Novye Dannye o Mineralakh SSSR (Proceedings of Fersman Mineralogical Museum)*, **18**, 206–209 [in Russian].
- Kutlu I. and Meyer G. (1999) Basische Carbonate des Dysprosiums: $\text{Dy}_2\text{O}_2(\text{CO}_3)$ und $\text{Dy}(\text{OH})(\text{CO}_3)$. *Zeitschrift für Anorganische und Allgemeine Chemie*, **625**, 402–406.
- Lacroix A. (1912) Sur l'existence de la bastnaesite dans les pegmatites de Madagascar. Les propriétés de ce mineral. *Bulletin de la Société Française de Minéralogie*, **35**, 108–113.
- Levinson A.A. (1966) A system of nomenclature for rare-earth minerals. *American Mineralogist*, **51**, 152–158.
- Maksimović Z. and Pantó G. (1983) Mineralogy of yttrium and lanthanide elements in karstic bauxite deposits. *Travaux du Comité International pour l'Etude des Bauxites, de l'Alumine et de l'Aluminium*, **13**, 191–200.
- Maksimović Z. and Pantó G. (1985) Hydroxyl-bastnaesite-(Nd), a new mineral from Montenegro, Yugoslavia. *Mineralogical Magazine*, **49**, 717–720.
- Mandarino J.A. (1981) The Gladstone-Dale relationship. Part IV. The compatibility concept and its application. *The Canadian Mineralogist*, **14**, 498–502.

- Mi J., Shen J., Pan B. and Liang J. (1996) Crystal structure refinement of bastnäsite-(Ce) and fluocerite-(Ce). *Earth Science – Journal of China University of Geosciences*, **21**, 63–67 [in Chinese with English abstract].
- Michiba K., Tahara T., Nakai I., Miyawaki R. and Matsubara S. (2011) Crystal structure of hexagonal RE(CO₃)OH. *Zeitschrift für Kristallographie*, **226**, 518–530.
- Michiba K., Miyawaki R., Minakawa T., Terada Y., Nakai I. and Matsubara S. (2013) Crystal structure of hydroxylbastnäsite-(Ce) from Kamihouri, Miyazaki Prefecture, Japan. *Journal of Mineralogical and Petrological Sciences*, **108**, 326–334.
- Minakawa T., Adachi T. and Matsuda M. (1992) Hydroxylbastnaesite-(Ce), a new occurrence from Japan. *Chigaku Kenkyu*, **41**, 155–159.
- Mineev D.A., Lavrishcheva T.I. and Bykova A.V. (1970) Yttrium bastnaesite, a product of gagarinite alteration. *Zapiski Vsesoyuznogo Mineralogicheskogo Obshchestva*, **99(3)**, 328–332 [in Russian].
- Miyawaki R., Matsubara S., Yokoyama K., Iwano S., Hamasaki K. and Yukinorii I. (2003) Kozoite-(La), La(CO₃)(OH), a new mineral from Mitsukoshi, Hizen-cho, Saga Prefecture, Japan. *Journal of Mineralogical and Petrological Sciences*, **98(4)**, 137–141.
- Miyawaki R., Yokoyama K. and Husdal T.A. (2013) Bastnäsite-(Nd), a new Nd-dominant member of the bastnäsite group from the Stetind pegmatite, Tysfjord, Nordland, Norway. *European Journal of Mineralogy*, **25**, 187–191.
- Nakamoto K. (2008) *Infrared and Raman Spectra of Inorganic and Coordination Compounds, Theory and Applications in Inorganic Chemistry*. John Wiley and Sons, NY. 350 pp.
- Ni Y., Hughes J.M., and Mariano A.N. (1993) The atomic arrangement of bastnäsite-(Ce), Ce(CO₃)F, and structural elements of synchysite-(Ce), röntgenite-(Ce), and parisite-(Ce). *American Mineralogist*, **78**, 415–418.
- Oftedal I. (1931) Zur Kristallstruktur von Bastnäsit (Ce,La)FCO₃. *Zeitschrift für Kristallographie, Mineralogie und Petrographie*, **78**, 462–469.
- Ondrejka M., Uher P., Pršek J., Ozdín D. and Putiš M. (2005) Arsenian monazite-(Ce) and REE arsenates and carbonates: Composition and substitution in the REEPO₄ – REEAsO₄ system. Example from Tisovec – Rejkovo thiolite (Western Carpathians, Slovakia). *Geophysical Research Abstracts*, Vol. 7, 04857.

- Pantó G. and Maksimović Z. (2001) Two new rare earth minerals in an unusual mineralization of the Nissi bauxite deposit, Greece. *Acta Geologica Hungarica*, **44**(1), 81–93.
- Pekov I.V. (1998) *Minerals First Discovered on the Territory of the Former Soviet Union*. OP, Moscow, 369 pp.
- Pekov I.V., Alimova A.N., Kononkova N.N. and Kanonerov A.A. (2002) On the mineralogy of Mochalin Log at Southern Urals I. Minerals of the bastnäsite family: history of studies and new data. *Uralskiy Geologicheskij Zhurnal (Uralian Geological Journal)*, **4**(28), 127–144 [in Russian].
- Pekov I.V., Zubkova N.V., Kasatkin A.V., Chukanov N.V., Koshlyakova N.N., Ksenofontov D.A., Škoda R., Britvin S.N., Kirillov A.S., Zaitsev A.N., Kuznetsov A.M. and Pushcharovsky D.Y. (2021) Hydroxylbastnäsite-(La), IMA2021–001. CNMNC Newsletter 61. *Mineralogical Magazine*, **85**, 461.
- Petříček V., Dušek M. and Palatinus L. (2006) *Jana2006. Structure Determination Software Programs*. Institute of Physics, Praha, Czech Republic.
- Rudnev V.V., Chukanov N.V., Nechelyustov G.N. and Yamnova N.A. (2007) Hydroxylborite, $Mg_3(BO_3)(OH)_3$, a new mineral species and isomorphous series fluoborite-hydroxylborite. *Geology of Ore Deposits*, **49**, 710–719.
- Silberminz V. (1929) Sur le gisement de cerite, de bastnäsite et d'un minéral nouveau la lessingite dans le district minier de Kychtym (Oural). *Comptes Rendus de l'Academie des Sciences de Russie*, A, **3**, 55–60 [in French].
- Strunz H. (1962) *Mineralogicheskie Tablitsy (Mineralogical Tables, with additions by A.S. Povarennykh)*. Gosgortekhzdat, Moscow [in Russian].
- Svyazhin N.V. (1965) Kyshtymite as a bastnäsite variety. *Trudy Instituta Geologii Uralskogo Filiala AN SSSR (Proceedings of the Institute of Geology of the Uralian Branch of Academy of Sciences of USSR)*, **70**, 249–252 [in Russian].
- Terada Y., Nakai I. and Kawashima T. (1993) Crystal structure of bastnäsite (Ce,La,Nd,Sm,Gd)CO₃F. *Analytical Sciences*, **9**, 561–562.
- Warr L.N. (2021) IMA-CNMNC approved mineral symbols. *Mineralogical Magazine*, **85**, 291–320.

- White T., Ferraris C., Kim J. and Srinivasan M. (2005) Apatite – an adaptive framework structure. In: *Micro- and Mesoporous Mineral Phases* (G. Ferraris and S. Merlino, eds.). *Reviews in Mineralogy and Geochemistry*, **57**, 307–402.
- Wang Y., Nestola F., Hou Z., Miyawaki R., Pekov I.V., Gu X., Dong G. and Qu K. (2024) Nomenclature of the ancylite supergroup. *Mineralogical Magazine*, **88**, in press. DOI: 10.1180/mgm.2024.8
- Yang H., Dembowski R.F., Conrad P.G. and Downs R.T. (2008) Crystal structure and Raman spectrum of hydroxyl-bastnäsite-(Ce), $\text{CeCO}_3(\text{OH})$. *American Mineralogist*, **93**, 698–701.

Prepublished Article

Table 1. Chemical composition (in wt.%) of hydroxylbastnäsite-(La).

Constituent	Holotype (Vuoriharvi)		Cotype (Mochalin Log)		Probe standard
	Average*	Range / SD	Average**	Range / SD	
CaO	0.23	0.08 – 0.28 / 0.08	-	-	CaSiO ₃
SrO	0.07	0.03 – 0.14 / 0.04	-	-	SrSO ₄
La ₂ O ₃	39.47	36.85 – 42.01 / 2.05	39.58	39.44 – 39.73 / 0.15	LaPO ₄
Ce ₂ O ₃	33.51	31.75 – 35.17 / 1.34	31.99	31.75 – 32.12 / 0.21	CePO ₄
Pr ₂ O ₃	1.03	0.97 – 1.07 / 0.05	1.51	1.37 – 1.70 / 0.17	PrPO ₄
Nd ₂ O ₃	1.95	1.54 – 2.45 / 0.37	2.38	2.26 – 2.52 / 0.13	NdPO ₄
F	0.76	0.61 – 0.91 / 0.12	3.33	3.21 – 3.45 / 0.12	MgF ₂ ***
CO _{2calc.}	20.49		20.34		
H ₂ O _{calc.}	3.77		2.58		
–O=F	0.32		1.40		
Total	100.96		100.31		

*For five spot analyses; **for three spot analyses; ***for the cotype specimen, topaz was used as probe standard for F. SD – standard deviation. Dash means that the content is below detection limit.

Table 2. Powder X-ray diffraction data (d in Å) of holotype hydroxylbastnäsite-(La).

I_{obs}	d_{obs}	I_{calc}^*	d_{calc}	hkl
39	4.98	51	4.984	002
88	3.616	81	3.619	300
100	2.926	100	2.928	302
5	2.650	2	2.653	222
2	2.591	1	2.582	123
1	2.577	0.5	2.577	132
9	2.490	11	2.492	004
		0.5	2.490	230
5	2.304	3	2.305	411
1	2.278	1	2.280	223
2	2.235	1	2.231	133
3	2.138	1	2.140	412

41	2.089	33	2.090	330
46	2.052	50	2.052	304
40	1.927	1	1.929	413
		34	1.927	332
14	1.809	12	1.810	600
24	1.701	20	1.701	602
2	1.663	0.5	1.662	135
		2	1.661	006
16	1.601	15	1.601	334
8	1.509	11	1.510	306
12	1.464	11	1.464	604
9	1.368	8	1.368	360
20	1.319	17	1.319	362
7	1.300	7	1.300	336
1	1.244	2	1.246	008
6	1.224	7	1.224	606
3	1.207	4	1.207	900
14	1.199	14	1.199	364
		5	1.178	308
9	1.173	7	1.173	902
6	1.086	6	1.086	904
4	1.070	5	1.070	338
7	1.056	11	1.056	366
		1	1.048	357
4	1.045	3	1.045	660
		5	1.026	608
6	1.023	6	1.023	662

*For the calculated pattern, only reflections with intensities ≥ 0.5 are given; the strongest reflections are marked in boldtype.

Table 3. Coordinates and isotropic displacement parameters (U_{iso} , in \AA^2) of atoms for holotype hydroxylbastnäsite-(La).

Site	x	y	z	U_{iso}
<i>REE1</i>	0.112(6)	0.226(3)	0.240(3)	0.0112(10)
<i>REE2</i>	0.438(3)	0.217(4)	0.257(3)	0.0112(10)
<i>REE3</i>	0.1042(12)	0.560(3)	0.264(3)	0.0112(10)
C1	0.481801	0.35345	0	0.012
C2	0.200085	0.084242	0	0.012
C3	0.299288	0.459352	0	0.012
C4	0.549888	0.422032	0.5	0.012
C5	0.229944	0.45779	0.5	0.012
C6	0.198725	0.036634	0.5	0.012
O1	0.478(15)	0.244(7)	0	0.011(9)
O2	0.486(6)	0.403(4)	0.1139(14)	0.011(9)
O3	0.033(2)	0.160(15)	0	0.011(9)
O4	0.238(18)	0.15(3)	0.11(2)	0.011(9)
O5	0.081(12)	0.578(2)	0	0.011(9)
O6	0.252(5)	0.419(6)	0.1155(9)	0.011(9)
O7	0.49(4)	0.3041(8)	0.5	0.011(9)
O8	0.524(18)	0.100(9)	0.386(10)	0.011(9)
O9	0.3497(5)	0.52(2)	0.5	0.011(9)
O10	0.17(3)	0.425(17)	0.39(2)	0.011(9)
O11	0.074(5)	0.168(11)	0.5	0.011(9)
O12	0.250(12)	0.072(14)	0.385(4)	0.011(9)
O13 = OH	0	0	0.28(2)	0.011(9)
O14 = OH	2/3	1/3	0.24(4)	0.011(9)
O15 = OH	1/3	2/3	0.26(5)	0.011(9)
O16 = OH	0.322(4)	0.320(2)	0.332(8)	0.011(9)
O17 = OH	0.338(4)	-0.003(4)	0.189(12)	0.011(9)

Table 4. Selected interatomic distances (Å) in the structure of holotype hydroxylbastnäsite-(La).

<i>REE1</i> - O3	2.56(5)	<i>REE3</i> - O2	2.59(8)
- O4	2.6(3)	- O5	2.67(4)
- O6	2.50(6)	- O6	2.55(6)
- O10	2.6(2)	- O8	2.59(10)
- O11	2.66(4)	- O9	2.56(4)
- O12	2.51(13)	- O10	2.6(3)
- O13	2.49(5)	- O15	2.492(14)
- O16	2.46(8)	- O16	2.53(7)
- O17	2.48(10)	- O17	2.49(7)
< <i>REE1</i> - O>	2.54	< <i>REE3</i> - O>	2.56
<i>REE2</i> - O1	2.60(3)		
- O2	2.54(6)	C1 - O1	1.36(11)
- O4	2.6(2)	- O2	1.28(3) x 2
- O7	2.60(4)	<C1-O>	1.31
- O8	2.5(2)		
- O12	2.50(9)	C2 - O3	1.29(4)
- O14	2.49(4)	- O4	1.3(2) x 2
- O16	2.49(7)	<C2-O>	1.30
- O17	2.48(7)		
< <i>REE2</i> - O>	2.53	C3 - O5	1.35(3)
		- O6	1.28(2) x 2
		<C3-O>	1.30
		C4 - O7	1.280(10)
		- O8	1.26(14) x 2
		<C4-O>	1.27
		C5 - O9	1.301(8)
		- O10	1.3(2) x 2
		<C5-O>	1.30
		C6 - O11	1.34(7)
		- O12	1.28(6) x 2
		<C6-O>	1.30

Table 5. Comparative data of hydroxylbastnäsite-(La), hydroxylbastnäsite-(Ce), bastnäsite-(La) and bastnäsite-(Ce)

Mineral	Hydroxyl- bastnäsite-(La)*	Hydroxyl- bastnäsite-(Ce)	Bastnäsite-(La)	Bastnäsite-(Ce)
Ideal formula	La(CO ₃)(OH)	Ce(CO ₃)(OH)	La(CO ₃)F	Ce(CO ₃)F
Crystal system	Hexagonal	Hexagonal	Hexagonal	Hexagonal
Space group	<i>P</i> -6	<i>P</i> -6**	<i>P</i> -62 <i>c</i>	<i>P</i> -62 <i>c</i>
<i>Unit cell data:</i>				
<i>a</i> , Å	12.537(3)	12.41 – 12.47	7.12 – 7.16	7.08 – 7.12
<i>c</i> , Å	9.968(2)	9.85 – 9.96	9.67 – 9.81	9.72 – 9.76
<i>V</i> , Å ³	1357(5)	1314 – 1342	424 – 436	421 – 428
<i>Z</i>	18	18	6	6
<i>Optical data:</i>	Uniaxial (+)	Uniaxial (+)	Uniaxial (+)	Uniaxial (+)
ω	1.76(1)	1.760	1.714 – 1.717	1.717 – 1.722
ε	1.86(1)	1.870	1.818	1.818 – 1.823
Sources	This work	Kirillov, 1964, 1966; Yang <i>et al.</i> , 2008; Michiba <i>et al.</i> , 2013	Kupriyanova, 1968; Pekov <i>et al.</i> , 2002; Anthony <i>et al.</i> , 2003	Aleksandrov, 1965; Ni <i>et al.</i> , 1993; Terada <i>et al.</i> , 1993; Anthony <i>et al.</i> , 2003; Miyawaki <i>et al.</i> , 2013

*Data for holotype. **Both natural samples of hydroxylbastnäsite-(Ce) with determined crystal structure possess the space group *P*-6 and unit-cell parameters $a = 12.41 - 12.47$ and $c = 9.85 - 9.96$ Å ($Z = 18$) (Yang *et al.*, 2008; Michiba *et al.*, 2013) [synthetic bastnäsite-like hydroxyl-carbonates $REE(CO_3)(OH)$ with $REE =$ trivalent La, Pr, Nd, Sm, Eu, Gd, Tb, Dy, Ho, Er have the same space group and unit-cell metrics: Christensen, 1973; Kutlu and Meyer, 1999; Michiba *et al.*, 2011], whereas in older publications, hydroxylbastnäsite-(Ce) and hydroxylbastnäsite-(Nd) were reported, by analogy with a fluorine-rich bastnäsites, with the hexagonal unit cell with parameters $a = 7.19 - 7.23$ and $c = 9.92 - 9.98$ Å ($Z = 6$) (Kirillov, 1964, 1966; Aleksandrov, 1965; Maksimović and Pantó, 1985; Minakawa *et al.*, 1992), and the space group *P*-62*c*, found for the structurally studied F-rich members of the bastnäsite-(Ce) – bastnäsite-(La) series (Ofstedal, 1931; Donnay and Donnay, 1953), was also suggested in this period for hydroxylbastnäsites (Anthony *et al.*, 2003).

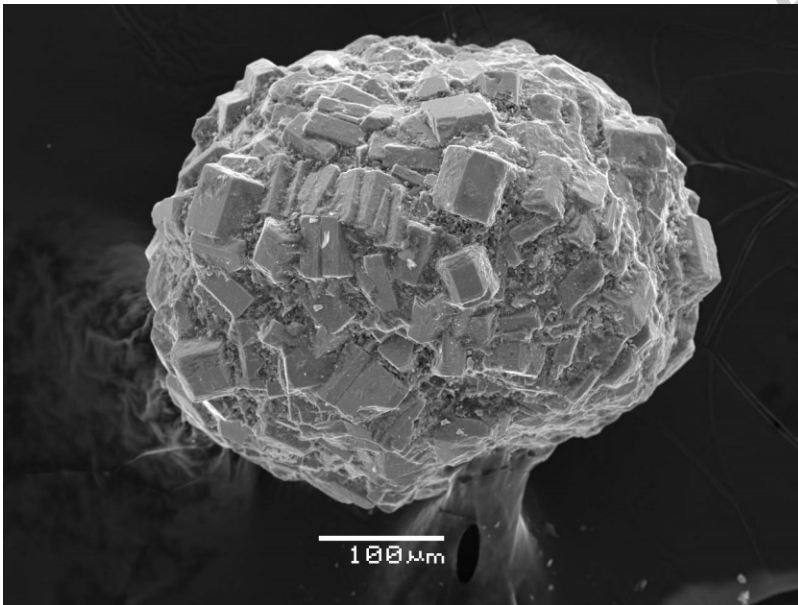
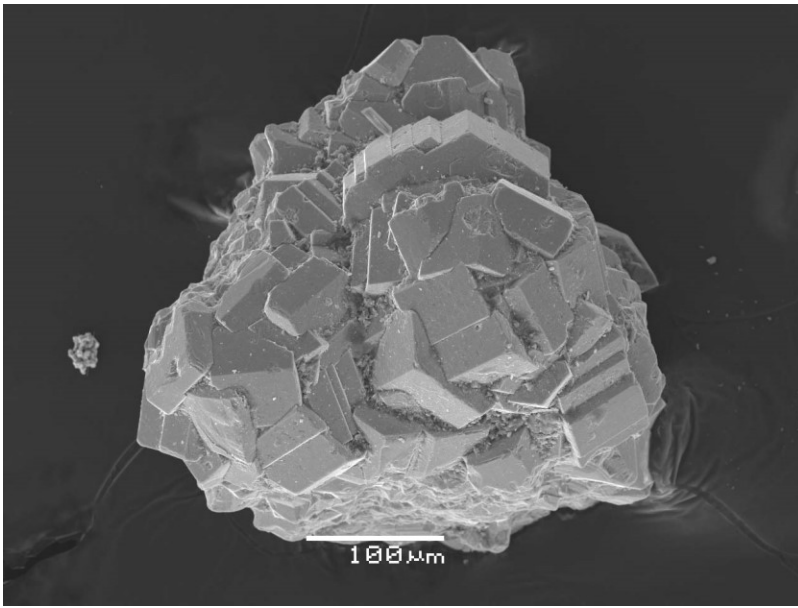


Figure 1. Clusters of hydroxylbastnäsite-(La) crystals from Vuoriyarvi. Holotype specimen. SEM (secondary electron) images.

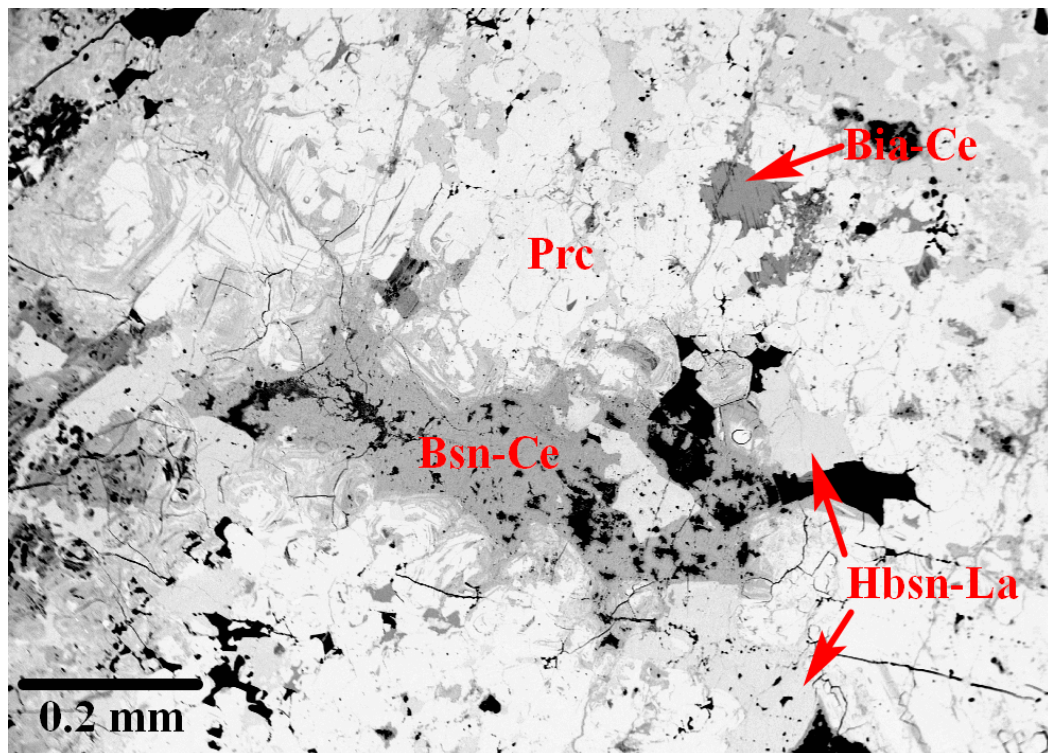


Figure 2. Hydroxylbastnäsite-(La) (Hbsn-La) grains in aggregate of other *LREE* minerals and quartz (black areas) from Mochalin Log. Prc – percleveite-(Ce) / percleveite-(La), Bsn-Ce – Ca-enriched variety of bastnäsite-(Ce), Bia-Ce – biraite-(Ce). Cotype specimen. Polished section, SEM (backscattered electron) image.

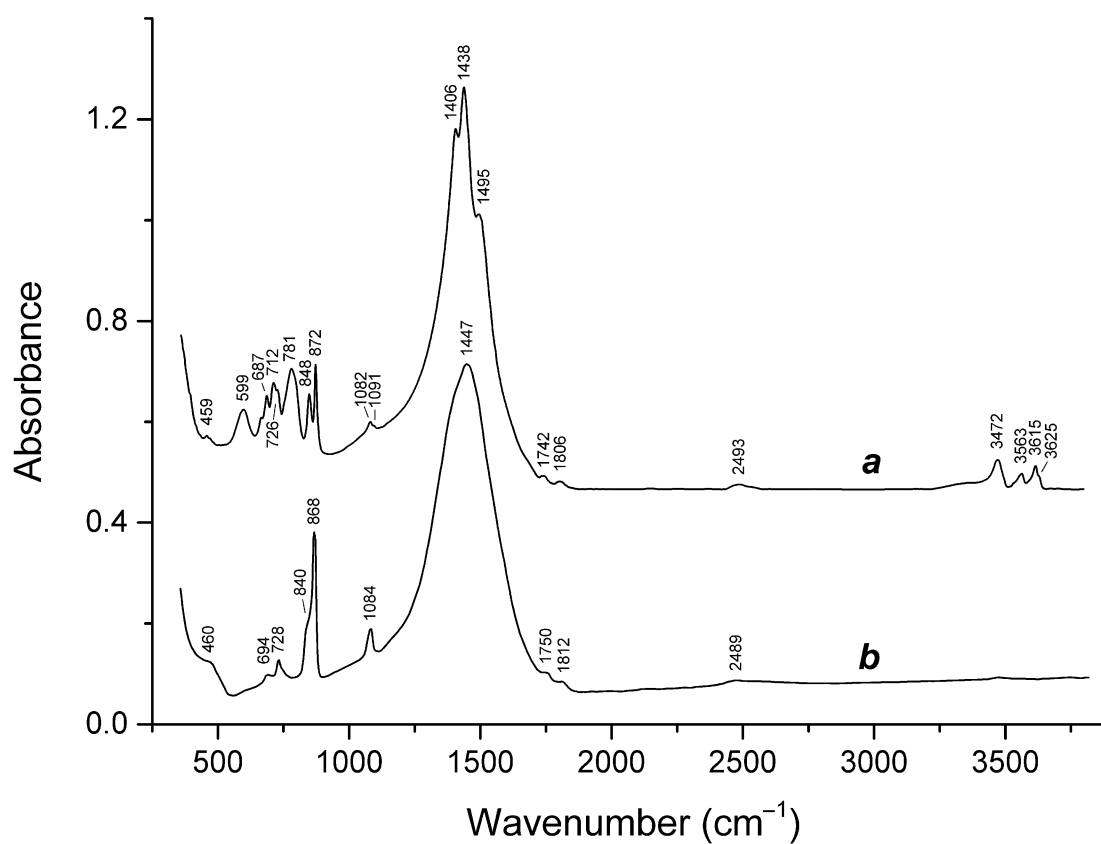


Figure 3. Powder infrared absorption spectra of **(a)** holotype hydroxylbastnäsite-(La) from Vuoriyarvi and **(b)** bastnäsite-(Ce) with the composition $(\text{Ce}_{0.54}\text{La}_{0.26}\text{Nd}_{0.12}\text{Pr}_{0.06}\text{Sm}_{0.01}\text{Ca}_{0.01})_{\Sigma 1}(\text{CO}_3)\text{F}_{0.98}(\text{OH})_{0.01}$ from Mt. Ploskaya, Western Keivy, Kola Peninsula, Russia.

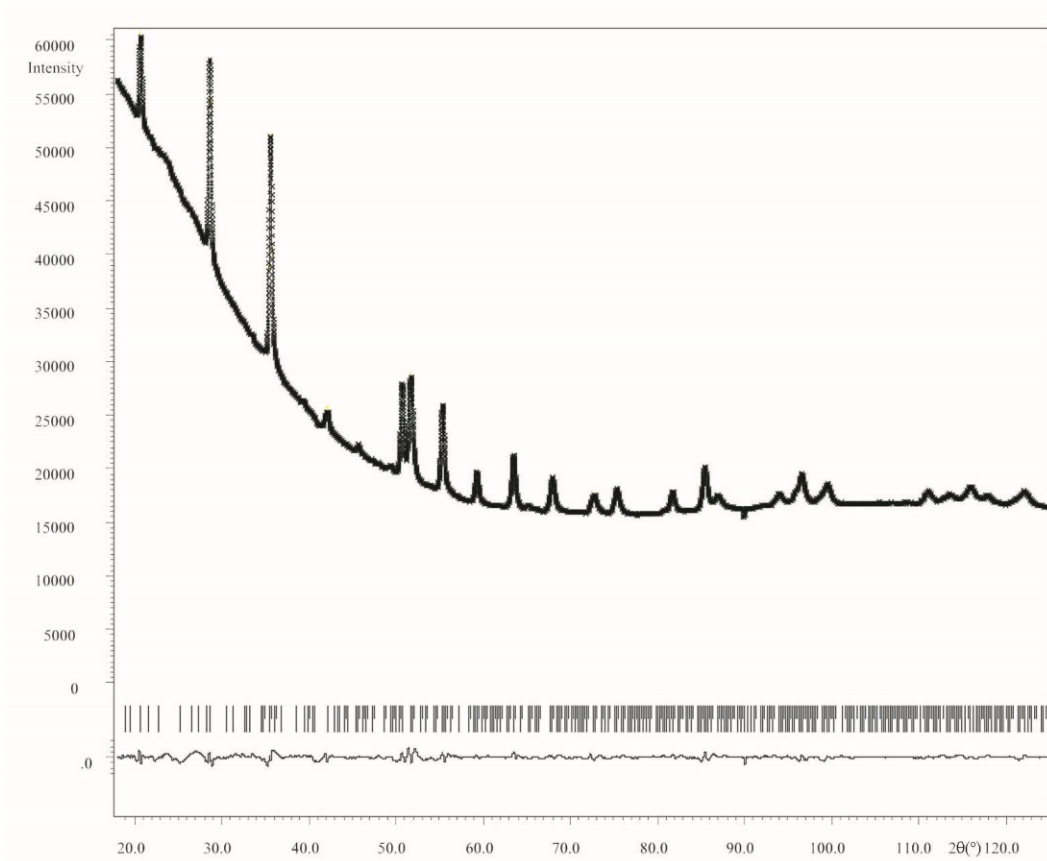
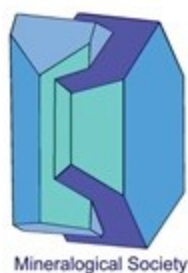


Figure 4. Observed and calculated powder X-ray diffraction patterns of hydroxylbastnäsite-(La). The solid line corresponds to calculated data, the crosses correspond to the observed pattern, vertical bars mark all possible Bragg reflections. The difference between the observed and calculated patterns is shown by curve at the bottom.




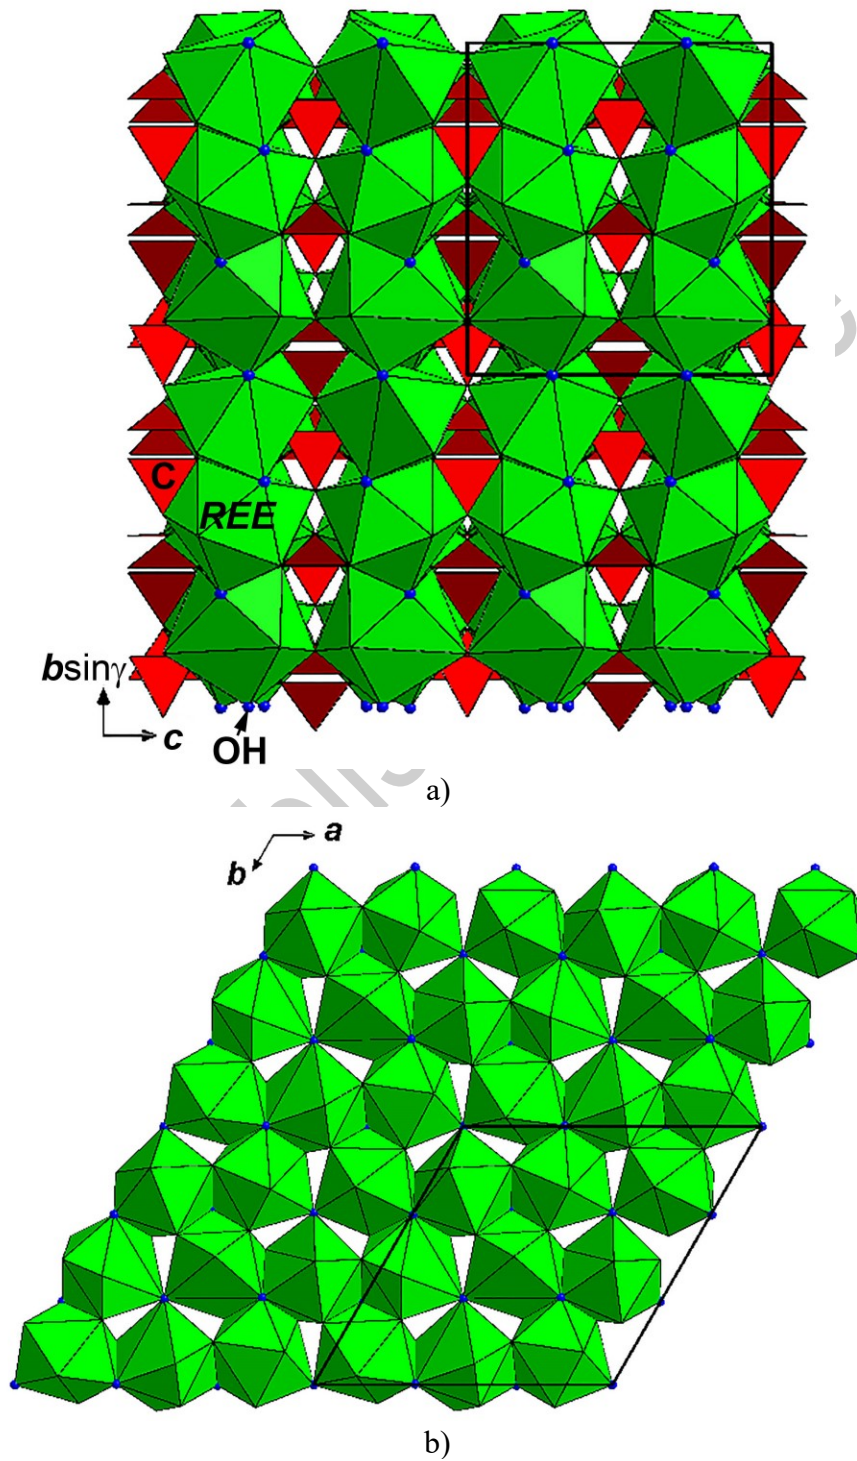


Figure 5. The crystal structure of hydroxylbastnäsite-(La) projected along the *a* axis (a) and the

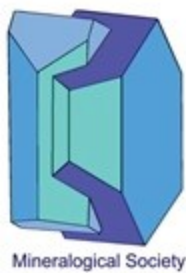

This is a 'preproof' accepted article for Mineralogical Magazine. This version may be subject to change during the production process.
DOI: 10.1180/mgm.2024.65

layer of *REE*-centred polyhedra in it (b). The unit cell is outlined.

Prepublished Article

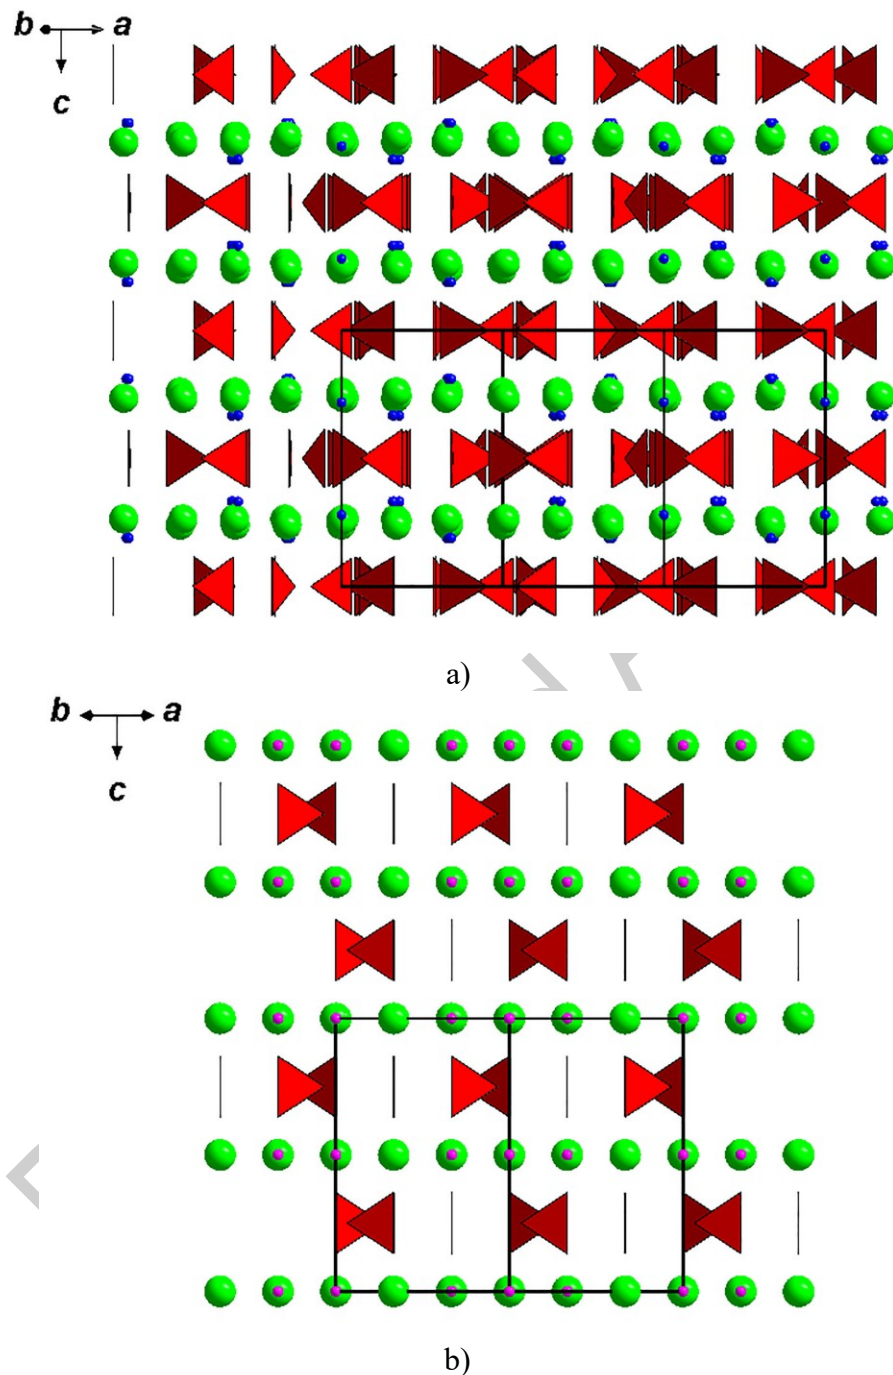


Figure 6. The crystal structures of hydroxylbastnäsite-(La) (projected along [120]; a) and bastnäsite-(Ce) (projected along [110]; b: drawn after Donnay and Donnay, 1953). For legend see Fig. 5; fluorine atoms in bastnäsite-(Ce) are shown as small reddish-pink circles. The unit cells are outlined.